



IRAJ INTERNATIONAL JOURNALS

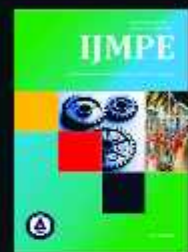

IJMPE

www.ijmpe.iraj.in


International Journal of Mechanical and Product Engineering
ISSN(P):2320-2092
ISSN(e):2321-2071

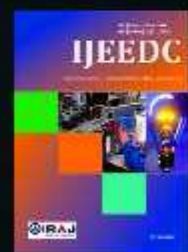

IJEEDC

www.ijeedc.iraj.in

International Journal of Electrical, Electronics and Data Communication
ISSN(P):2320-2084
ISSN(e):2321-2950

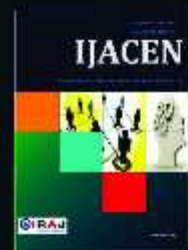

IJACEN

www.ijacen.iraj.in

International Journal of Advance Computational Engineering and Networking
ISSN(e):2320-2106
ISSN(P):2320-2106

Conference Partners



International Journal of Soft Computing And Artificial Intelligence (IJSCAI)

ISSN(P):2321-404X
ISSN(e):2321-4384
www.ijscai.iraj.in



International Journal of Advances in Computer Science and Cloud Computing (IJACSCC)

ISSN(P):2321-4058
ISSN(e):2321-4392
www.ijacsc.com



International Journal of Advances in Science, Engineering and Technology (IJASEAT)

ISSN(P):2321-8991
ISSN(e):2321-9009
www.ijaseat.iraj.in



International Journal of Industrial Electronics and Electrical Engineering (IJIEEE)

ISSN(P):2347-6982
ISSN(e):2349-204X
www.ijiee.iraj.in



International Journal of Advances in Mechanical and Civil Engineering (IJAMCE)

ISSN(P):2394-2827
www.ijamce.iraj.in



International Journal of Management and Applied Science (IJMAS)

ISSN(P):2394-7926
www.ijmas.iraj.in



International Journal of Advance in Electronics and Computer Science (IJAECs)

ISSN(P):2393-2835
www.ijaecs.iraj.in

IRAJ Journals Listed in University Library

MIT, University of California Berkeley, Stanford, Cambridge, Oxford, Harvard

Visit for Upcoming Conferences - www.academicworld.org



This book will be available online at
World Research Library
www.worldresearchlibrary.org

ISBN



978-93-89469-66-0

PROCEEDINGS OF



Academics World

INTERNATIONAL CONFERENCE



Association With



Bandar Seri Begawan
Brunei Darussalam

11th - 12th March - 2020

PROCEEDINGS OF
ACADEMICS WORLD
INTERNATIONAL CONFERENCE
BANDAR SERI BEGAWAN,
BRUNEI DARUSSALAM

Organized by



Date of Event:
11th – 12th March, 2020

Event Co-Sponsored by



Corporate Address

INSTITUTE OF RESEARCH AND JOURNALS

Plot No- 30, Dharma Vihar, Khandagiri, Bhubaneswar, Odisha, India

Mail: info@iraj.in, www.iraj.in

Publisher: **Institute for Technology and Research (ITRESEARCH)**

© 2020, Academics World International Conference, Bandar Seri Begawan, Brunei Darussalam

No part of this book can be reproduced in any form or by any means without prior written permission of the publisher.

Disclaimer: Authors have ensured sincerely that all the information given in this book is accurate, true, comprehensive, and correct right from the time it has been brought in writing. However, the publishers, the editors, and the authors are not to be held responsible for any kind of omission or error that might appear later on, or for any injury, damage, loss, or financial concerns that might arise as consequences of using the book.

Type set & printed by:

Institute for Technology and Research (ITRESEARCH)

Bhubaneswar, India

About IRAJ:

Institute of Research and Journal (IRAJ) is an advanced Non-profit technological forum registered under Peoples Empowerment Trust, situated at Bhubaneswar, Odisha, for the Researchers & Scholars “to promote the progress of Science and Technology” by displaying their knowledge in the vicinity of Science and Technology for the service of mankind and the advancement of the general welfare.

Objective of IRAJ:

- ❖ To provide a world class platform to researchers to share the research findings by organizing International/National Conferences.
- ❖ To use the research output of the conference in the class room for the benefits of the students.
- ❖ To encourage researchers to identify significant research issues in identified areas, in the field of Science, Engineering, Technology and Management.
- ❖ To help dissemination of their work through publications in a journal or in the form of conference proceedings or books.
- ❖ To help them in getting feedback on their research work for improving the same and making them more relevant and meaningful, through collective efforts.
- ❖ To encourage regional and international communication and collaboration; promote professional interaction and lifelong learning; recognize outstanding contributions of individuals and organizations; encourage scholar researchers to pursue studies and careers in circuit branches and its applications.
- ❖ To set up, establish, maintain and manage centers of excellence for the study of /on related subjects and discipline and also to run self supporting projects for the benefit of needy persons, irrespective of their caste, creed or religion.

About Academics World:

Academics World is a non-profit organization that promotes the Engineering and Technology, Science and Medical related latest developments and issues to be discussed and experimented through interactions amongst the researchers and academician across the globe at a common platform in association with IRAJ & The IIER.

Conference Committee

Program Chair:

Dr. P. Suresh

M.E, Ph.D. Professor and Controller of Examinations,
Karpagam College of Engineering.,
Coimbatore, India.

Conference Manager:

Mr. Bijan Kumar Barik

Mob: +91-9776047497

Conference Convener:

Miss. Madhusmita Satapathy, Academics World

Mob: +91 7077656338

Publication Head:

Mr. Manas Ranjan Prusty, IRAJ, India

INTERNATIONAL ADVISORY MEMBERS

Prof. Goodarz Ahmadi,

Professor, Mechanical and Aeronautical Engineering, Clarkson University, USA

Dr Chi Hieu Le,

Senior Lecturer, University of Greenwich. Kent ME4 4TB. United Kingdom

PROF. (ER.) Anand Nayyar

Department of Computer Applications & I.T.KCL Institute of Management and Technology, Jalandhar
G.T. Road, Jalandhar-144001,Punjab, India.

Prof. R. M. Khaire,

Professor, Dept. Of Elex. and Telecommunication, B, V University, India

Mark Leeson

Associate Professor (Reader)

Area of Expertise: nanoscale communications,
evolutionary algorithms, network coding and communication systems

Dr. P. K. Agarwal

Professor, Deptt. of Civil Engineering, MANIT Bhopal ,Ph. D: IIT Kanpur
M.E: Civil Engg.IIT Roorkee, Membership: Indian Road Congress (IRC), Institute of Urban Transport (IUT)

Shahriar Shahbazpanahi

Islamic Azad University,
Department of Civil Engineering, Sanandaj, Kurdistan, Iran, PhD (Structural Engineering),
University Putra Malaysia, Malaysia , 2009-Present

Harun Bin Sarip

Head of Research and InnovationDept, UniKL-MICET

Doctorate: Université de La Rochelle, France

Member: International Society of Pharmaceutical Engineer, Singapore Chapter

Dr. Md. Al-Amin Bhuiyan

Associate Professor

Dept. of Computer Engineering

King Faisal University

Al Ahssa 31982, Saudi Arabia

Prof. (Er.) Anand nayyar

Department of Computer Applications & I.T.

KCL Institute of Management and Technology, Jalandhar

G.T. Road, Jalandhar-144001, Punjab, India

Prof. Aleksandr Cariow

Institution or Company: West Pomeranian University of
Technology, Szczecin

Dr. VPS Naidu

Principal Scientist & Assoc. Prof., MSDF Lab, FMCD
CSIR - National Aerospace Laboratories, Bangalore, India

Mr. P. Sita Rama Reddy

Chief Scientist ,Mineral Processing Department, CSIR - Institute of Minerals & Materials Technology
Bhubaneswar, India, M.Tech. (Chem. Engg., IIT, KGP)

Dr.P.C.Srikanth,

Professor & Head, E&C Dept, Malnad College of Engineering, Karnataka
Senior Member IEEE, Secretary IEEE Photonics Society,
M.Tech: IIT, Kanpur, Ph.D: In IISc Photonics lab

Prof. Lalit Kumar Awasthi,

Professor, Department of Computer Science & Engineering
National Institute of Technology(NIT-Hamirpur),
PhD, IIT, Roorkee, M. Tech, IIT, Delhi

Dr. Chandra Mohan V.P.

Assistant Professor, Dept. of Mech. Engg., NIT Warangal,
Warangal. Ph.D : Indian Institute of Technology(IIT),Delhi
M.B.A: Alagappa University

Prof. I.Suneetha,

Associate Professor, Dept. of ECE, AITS, Tirupati, India

Dr.s. Chandra Mohan Reddy,

Assistant Professor (SG) & Head,Dept. of Electronics & Communication Engineering, JNTUA College of Engineering, Pulivendula,
Ph.D,J.N.T. University Anantapur, Anantapuramu

Gurudatt Anil Kulkarni,

I/C HOD E&TC Department, MARATHWADA MITRA MANDAL'S POLYTECHNIC

Pasuluri Bindu Swetha

Dept. Of ECE, Stanley college of Engineering & Technology for Women, Hyderabad, India



TABLE OF CONTENTS

Sl No.	TITLES AND AUTHORS	Page No.
01.	Electrospinning of Chitosan/Poly (Vinyl Alcohol) Nanofibrous Membranes as An Alternative Wound Dressing Material ➤ <i>Harini Sosiati, Rafi Imam Ar-Rasyid, Parama Aji Darmawan, Krisdiyanto</i>	1-6
02.	Effect of 45-Degree Capillary Pipe Slope on Horizontal and Fluid Viscosity on The Water-Air Two-Phase Flow Pressure Gradient ➤ <i>Sukamta, Muhammad Rocky Pratama, Sudarja</i>	7-11
03.	Exploring Job Hopping Behavior Among Managers of Casual Dining Restaurants in Klang Valley Area, Malaysia ➤ <i>Hazrina Ghazali, Khairunnisa Mokhtar</i>	12-14
04.	The Strategic Management Process in Improving of Indonesian Defense Industries ➤ <i>Novky Asmoro, Khaerudin, Marsono, Supandi</i>	15-20
05.	Determination of Traffic Safety With Methods Alternative to Traditional Methods ➤ <i>Coruhemine, Tortum Ahmet</i>	21-26
06.	Advantage of Make-to-Stock Strategy Based on Linear Mixed-Effect Model ➤ <i>Yu-Pin Liao, Shin-Kuan Chiu</i>	27-38
07.	Faculty Researchers and Non-Researchers in the Context of Teaching Performance and Personal Profile ➤ <i>Jake M. Laguardor, Joseph Cezar L. Deligero, Cecilia C. Pring</i>	39-44
08.	Influence of The FLC'S Parameters of The UPQC in The Distributed Generation ➤ <i>C. Benachaiba, B. Mazari, M. Habab, C. Benoudjafer, N. M. Tandjaoui</i>	45-50

★★★

EDITORIAL

It is my proud privilege to welcome you all to the Academics World International Conference at Bandar Seri Begawan, Brunei Darussalam. I am happy to see the papers from all part of the world and some of the best paper published in this proceedings. This proceeding brings out the various Research papers from diverse areas of Science, Engineering, Technology and Management. This platform is intended to provide a platform for researchers, educators and professionals to present their discoveries and innovative practice and to explore future trends and applications in the field Science and Engineering. However, this conference will also provide a forum for dissemination of knowledge on both theoretical and applied research on the above said area with an ultimate aim to bridge the gap between these coherent disciplines of knowledge. Thus the forum accelerates the trend of development of technology for next generation. Our goal is to make the Conference proceedings useful and interesting to audiences involved in research in these areas, as well as to those involved in design, implementation and operation, to achieve the goal.

I once again give thanks to the Academics World, Institute of Research and Journals & The IIER for organizing this event in Bandar Seri Begawan, Brunei Darussalam. I am sure the contributions by the authors shall add value to the research community. I also thank all the International Advisory members and Reviewers for making this event a Successful one.

Editor-In-Chief

Dr. P. Suresh

M.E, Ph.D. Professor and Controller of Examinations,
Karpagam College of Engineering.,
Coimbatore, India.



ELECTROSPINNING OF CHITOSAN/POLY (VINYL ALCOHOL) NANOFIBROUS MEMBRANES AS AN ALTERNATIVE WOUND DRESSING MATERIAL

¹HARINI SOSIATI, ²RAFI IMAM AR-RASYID, ³PARAMA AJI DARMAWAN, ⁴KRISDIYANTO

^{1,2,3,4}Department of Mechanical Engineering, Faculty of Engineering, Universitas Muhammadiyah Yogyakarta, Jl. Brawijaya, Kasihan, Bantul, Yogyakarta 55183, Indonesia
E-mail: ¹hsosiati@ft.umy.ac.id, ²rafiimamarrasyid@gmail.com, ³paramagood@gmail.com, ⁴krisdiyanto@umy.ac.id

Abstract - A study of the influence of CS concentrations on the tensile properties corresponding to the fiber morphology formed in CS/PVA membranes is this research focus. The ability of the developed membranes for an alternative wound dressing material is also studied. The CS/PVA membranes were prepared using chitosan (CS) solution with different concentrations of (1, 3, 5, and 7 wt. %) combined with 10 wt. % poly (vinyl alcohol) (PVA) and a CS/PVA ratio of 5/95 by electro spinning method. The membranes with an optimized CS concentration of 3% and different CS/PVA ratios of 10/90, 15/85, and 20/80 were also studied. The membrane with 3 % CS concentration showed an optimum tensile strength (5.62 ± 0.47 MPa) with a CS/PVA ratio of 5:95. The improvement of the CS/PVA ratio increased the tensile strength and modulus of the membranes, which reached a maximum value (7.68 ± 1.94 MPa) at a CS/PVA ratio of 20:80, leading to a high density of tight bonds between the fibers. A simulation by finite element method (FEM) on the tensile properties of the CS/PVA membrane has shown that the membrane can be used as an alternative wound dressing material.

Keywords - Chitosan, PVA, Nanofibrous Membrane, Tensile Properties, Wound Dressing Material

I. INTRODUCTION

In the design of materials for some industrial applications, the achievement of the mechanical properties of the material, which is matching with the production target is one of the required product specifications. For example, the tensile properties of nanofiber membranes that are useful in certain applications such as food packaging and biomedical, should at least have a high strength and elasticity of the products. The rapid growth of nanofiber technology is the result of the nanotechnology revolution, which has made it possible to produce membranes from polymers. In this case, electro spinning is a simple method and useful for making polymer nanofibers. The simplicity of process technology in producing fiber in size from nanometer to sub-micro with a non-woven has made the preferred method. Related to the product of nanofiber membranes, a natural polymer of chitosan (CS) and a synthetic polymer of poly (vinyl alcohol) (PVA) were used as base materials in the current study. It is well known that chitosan produced from shrimp shell waste [1–3], is abundantly available in the earth, especially in the regions located near the sea. The effort to make efficient use of the waste is one of the environmental awareness.

In addition, chitosan is very useful in biomedical [4, 5] and food [6, 7] industries due to its advantageous characteristics such as biocompatible, non-toxic, antimicrobial, and biodegradable [8]. On the other hand, PVA is a semi-crystalline synthetic polymer and has almost the same as chitosan, except water solubility. Chitosan is insoluble in water, but soluble in acetic acid (CH_3COOH), whereas PVA, is

completely water-soluble, insoluble in the organic solvents and slightly soluble in alcohol [9, 10]. Therefore, a combination of CS and PVA is potentially also used for biomedical and food packaging applications. The studies of CS combined with PVA by electro spinning have been performed to address the characterization of the CS/PVA membrane properties and the use for wound dressing and wound healing [11–14]. The nanofiber membrane of the CS/PVA blend is better in mechanical properties than the neat PVA membrane and may be used in soft tissue engineering. The electrospun membranes made up of 1% chitosan and 10% PVA solutions combined with some different ratios of PVA/CS 80/20, 70/30, 60/40, and 50/50 were potential for wound care. The healing of the wound using the PVA/CS membrane was approximately 40% faster than the open wound [11]. PVA/CS nanofiber membrane tends to be an excellent material for wound dressing, it does not irritate the skin, although it has been in contact with the skin for a long duration (more than a few months) [12].

One % CS and 8% PVA solutions blended at the ratio of 50/50 resulted in a fiber structure closed to the natural tissues, indicating that it is capable of wound healing due to infection [13]. The CS/PVA nanofiber membrane at CS/PVA ratio of 25/75 and an average fiber of about 289 nm was very decisive in healing a diabetic wound on the mice [14]. However, few studies discussed the characterization of the tensile properties of CS/PVA nanofibrous membranes and the use of measurement properties for stress analysis. For wound dressing application, the mechanical property is one of the significant properties of the membrane. The membrane should have high strength,

sufficient modulus elasticity, and high strain, such as the properties of the natural tissue. When membranes are used, membranes may accept tensile loads. For example, if the membrane is used to cover the injury that occurred to the elbow or knee, and then the hand or legs are moved from a straight to a bent position, the membranes will receive a tensile load. It is, therefore, necessary to make the data of the tensile properties of the membranes and to perform the characterization and analysis. The current study discussed the tensile properties of the CS/PVA membranes affecting by the CS concentrations associated with the fiber morphology formed in the nanofibrous membranes. Besides, the capability of the membranes for alternative wound dressing material based on the data on tensile properties data was studied by a simulation using the finite element method (FEM) supported by Abaqus Simulia software. This analysis is required as the first step of confirmation before the membrane is produced for a commercial product.

II. DETAILS EXPERIMENTAL

2.1. Materials and Preparation of CS/PVA blend

Chitosan (CS) micro-powder and acetic acid (glacial, 99 – 100%) were obtained from Sigma-Aldrich and Merck, respectively. PVA (Gohsenol, Mw: 22,000 g/mol) was purchased from CV. Multi Kimia, Yogyakarta, Indonesia. Chitosan (CS) solutions with varying concentrations of 1, 3, 5, and 7 % (w/w) were prepared by dissolving chitosan micro-powder in the 2% (w/w) acetic acid solution. The dilution of the acetic acid solution was carried out at room temperature by stirring the solution at 200 rpm for 15 minutes. Subsequently, the dissolution of chitosan powder in the acetic acid solution was performed by heating the chitosan solution at around 80°C and magnetic stirring at 200 rpm for about 45 minutes and then cooling down to room temperature. In addition, the PVA solution was ready at a concentration of 10% (w/w).

2.2. Manufacture of the CS/PVA nanofiber membranes

The mixture of CS and PVA solutions used for the spinning solution was prepared in two types of CS/PVA blends, namely (1) CS/PVA blends at a CS/PVA ratio of 5/95 with 1, 3, 5 and 7 % CS concentrations, and (2) CS/PVA blends at 3% CS concentration with CS/PVA ratios of 5/95, 10/90, 15/85 and 20/80. The viscosity of all CS/PVA blends was measured with a Brookfield viscometer. All CS/PVA blends were inserted into the syringe in the electro spinning machine for the production of CS/PVA nanofiber membranes. The electro spinning process ran at an applied voltage of 18 kV, a fixed distance between the tip and the collector plate of

16.5 cm, a needle diameter of 0.6 mm, and a feed rate of ~0.5 ml/h.

2.3. Characterization

Scanning electron microscopy (SEM, Hitachi 3500-SU) was used to characterize the fiber morphologies of the produced membranes. The fiber diameter measurement was carried out by measuring at least 100 fibers on the SEM image using the ImageJ open-source software. The tensile test for all the membranes was carried out according to ASTM D-882, using a testing machine (Zwick Z0.5 Germany) at a crosshead speed of 10 mm/min and a gauge length of 20 mm. Seven membrane specimens with an average thickness of approximately 40 μm were prepared for each variation, in which the thickness was measured under an optical microscope (Olympus SZ 61).

2.4. Simulation

The simulation used the tensile properties of the second round of CS/PVA blending membranes. The membrane size of this simulation was modeled on the basis of a large-scale commercial band-aid: i.e., 60 mm in length and 30 mm in width. The use of the membrane in this research is to cover the wound near the elbow. When the position of the membrane moves from a straight position to be a bent position, the displacement will be occurred. This process is simulated and analyzed using the Abaqus Simulia software-supported FEM.

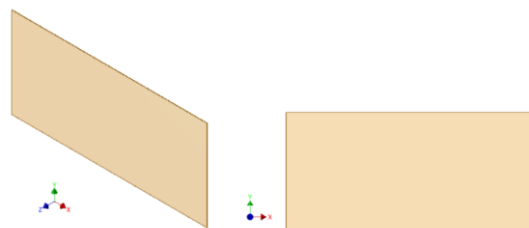


Fig.1. Geometric of the membrane.

In this simulation, the geometric of the membrane was firstly made (Fig.1). The geometric was then imported to the finite element-based software and given a force until the value of von mises is equivalent to the tensile strength of the used membrane.

III. RESULTS AND DISCUSSION

3.1. Optimization of CS Concentration

In the study of CS/PVA blend by electro spinning, the use of CS concentrations is different from each other. The CS concentration used in this study was optimized based on the result of

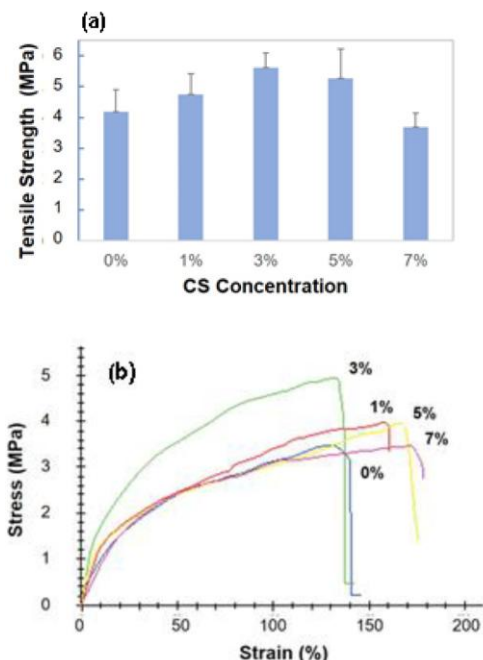


Fig.2. The tensile properties of CS/PVA nanofiber membrane at CS/PVA ratio of 5/95. (a) tensile strength vs CS concentration, and (b) stress-strain curve.

The tensile properties (Fig.2). In this case, the CS/PVA membrane with a concentration of 3% CS shows an optimum tensile strength value, whereas its elongation is almost the same as the elongation of the neat PVA. The elongation at break ranging from 100% to 150% seemed to be a part of the range of natural tissue properties. As a result, 3% of CS concentration was used to better classify CS/PVA mixtures by varying CS/PVA ratios. A study of the CS/PVA nanofibrous membrane with 3% CS concentration has achieved an optimum value of CS/PVA ratio at 50/50 based on better fiber structure formulation compared to other ratios [15]. Another research study varied the CS concentration from 0% to 3% to understand its effects on the formation of fiber during the electro spinning process. This research confirmed that the CS concentration of less than 2% and higher than 3% made the solution is not spinnable due to excessive viscosity of the solution [16- 17].

3.2. FTIR Analysis

The chemical structure of pure PVA, chitosan, and CS/PVA has different characteristics (Fig.3). The FTIR spectrum of pure PVA exhibits the main positions related to $-\text{OH}$ stretching (3364 cm^{-1}), $-\text{CH}$ stretching (2931 cm^{-1}), stretching vibration of $\text{C}=\text{O}$ groups (1735 cm^{-1}), $-\text{CH}$ bending (1427 cm^{-1}), $-\text{C}-\text{O}-$ stretching (1087 cm^{-1}) [18, 19]. In the spectrum of pure chitosan, the peaks at 3425 cm^{-1} and 2900 cm^{-1} are correspond to $-\text{OH}$ and $-\text{NH}_2$ stretching groups and $-\text{CH}$ stretching vibrations [18, 20]. The absorption bands identified at 1643 cm^{-1} , 1580 cm^{-1} and 1087 cm^{-1} are related to amide I, II,

and a weak amide III, respectively [21], while those positioned at 1087 cm^{-1} and 887 cm^{-1} are associated with $-\text{C}-\text{O}-$ stretching vibration [18]. The broad peak corresponding to $-\text{OH}$ stretching at approximately 3400 cm^{-1} is present in all spectra, which shifts to lower wave number as PVA content increases [19]. In the CS/PVA spectra, the coexistence of the functional groups of the $\text{C}=\text{O}$ groups, amide I, and II is represented in the CS/PVA (20/80) spectrum: i.e., at the positions of 1728 cm^{-1} , 1651 cm^{-1} , and 1566 cm^{-1} , respectively. Such results showed strong compatibility between CS and PVA in the CS/PVA nanofiber membranes. In the event that they are incompatible, the spectrum will show to be similar to the pure component one [19].

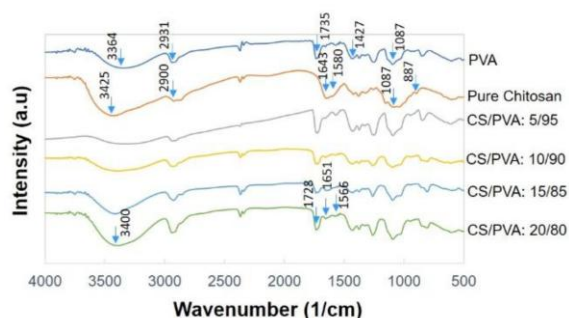


Fig.3. FTIR spectra of pure PVA and chitosan, and CS/PVA nanofibrous membranes at 3% CS concentration with various CS/PVA ratios.

3.3. Fiber morphology

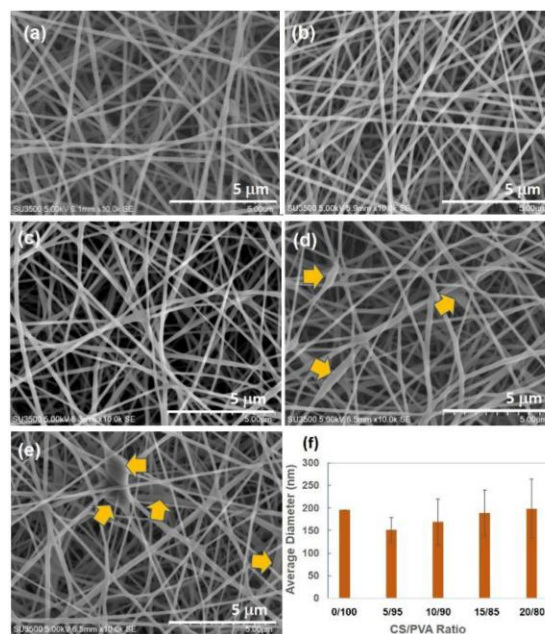


Fig.4. SEM images of nanofibrous membranes of CS/PVA blend with various CS/PVA ratios; 0/100 (a), 5/95 (b), 10/90 (c), 15/85 (d), 20/80 (e) showing the formation of beads in (d) and (e) (see arrows).

The fiber morphologies formed in all membrane specimens reveal straight-oriented fibers with a uniform size distribution, particularly at SC/PVA

ratio of 0/100 (neat-PVA) (Fig.4a) and 5/95 (Fig.4b). The higher the CS content, the larger the average fiber diameter (Fig.4f), which corresponds to the viscosity of CS-PVA spinning solutions (Table 1), which increases by increasing the CS concentration. The average fiber diameter of all CS/PVA fibrous membranes is in the range of 100 - 200 nm, which is proportional to a previous result [15]. Enhancing the viscosity of the spinning solution is not only providing an impact on the fiber diameter but also the formation of beads as fiber-defect, that has gradually been produced at CS/PVA ratio of more than 5/95 (Fig. 4d and 4e, see arrows). In this case, viscosity is a function of intermolecular interaction in the polymer structure. Thus, the viscosity of the solution has a significant impact on

Specimen at CS/PVA	Viscosity (cP)	Average fiber diameter (nm)
0/100	340	196
5/95	465	151
10/90	554	169
15/85	606	195
20/80	809	198

Table 1: Viscosity of the spinning solution of CS-PVA

the formation of fiber other than surface tension and electrical conductivity [22]. However, the beads formed in these membranes do not obstruct the cross linking of the fiber. It should be noted, therefore, that 3% of CS concentration yielded the appropriate viscosity of the solution resulting in good electrospinnability.

3.4. Tensile properties related to fiber morphologies

The fiber morphology in terms of fiber structure affects the tensile properties of the nanofibrous membranes. As far as our experience in the manufacture and characterization of the electro spun membranes is concerned, the fiber crosslink has positively played a crucial role in the tensile properties of the membranes. The higher the volume fraction of crosslink between fibers in the membrane, was formed, the higher the tensile strength of the membrane. Based on the present result (Fig.5a), the addition of chitosan gradually improved the tensile strength of the CS/PVA membranes, but the elongation varies (Fig.5b). The earlier result [15], which used around 2.5% CS concentration and different CS/PVA ratios showed comparable tensile strength (6.13 ± 0.72 MPa), significantly higher tensile modulus (94.2 ± 10.2 MPa) and lower elongation at break ($14.13 \pm 1.25\%$) at CS/PVA ratio of 15/85 compared to the present results. These measures were higher than the properties of CS/PVA membranes at CS/PVA ratios of 25/75 and 30/70, explaining that an increase of chitosan content yielded unfavorable tensile properties, especially for wound dressing material due to too high modulus

elasticity. Compared to another study [21], without the addition of chemical cross linking (tetraethyl ortho silicate/TEOS), these present results showed higher specifically in the tensile strength, but lower in the elongation at break. Besides, these tensile properties are also better than the other [23], although the chemical cross linking of glutaraldehyde (GA) has been used. In principle, the nanofibrous membrane with very high modulus elasticity is not applicable for wound dressing material. The tensile properties of these nanofiber membranes are used for the simulation analysis using Abaqus Simulia software in the next paragraph to ensure whether the produced membranes would be applicable for an alternative wound dressing material or not. Based on the result in Fig. 5a, the CS/PVA membrane with a CS/PVA ratio of 20/80 reaches the highest tensile strength (7.68 ± 1.94 MPa). This property was used for the following simulation.

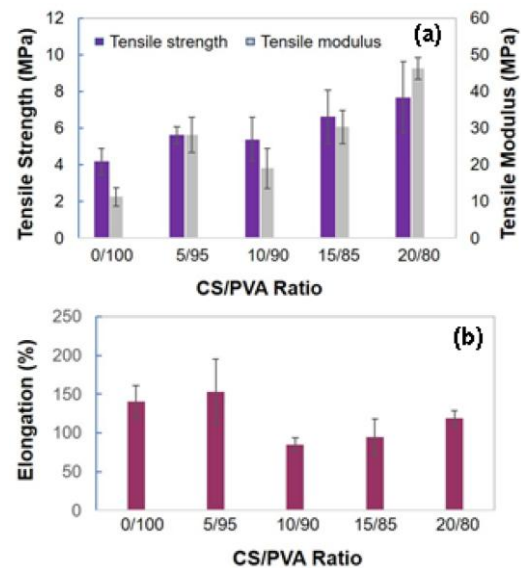


Fig.5. Tensile strength and modulus vs CS/PVA ratio (a) and elongation vs CS/PVA ratio (b).

3.5. A simulation result applied to the CS/PVA nanofiber membrane

The CS/PVA membrane with a CS/PVA ratio of 20/80 is selected for this simulation due to its highest tensile strength. The CS/PVA membrane application model in Fig. 6. displays the length of the membrane at a straight position of 60 mm. However, at a bent position, the range extends to be 65 mm, explaining that there is a displacement of about 5 mm toward x-direction. In this case, the trial and error were performed to determine the thickness of the membrane. The membranes with the dimension of 60 mm length, 30 mm width and various thicknesses from 40 μm to higher than 100 μm have been tried for modeling from a straight to the bent position. The results showed that the membrane had failed due to a thickness of less than 110 μm . Nevertheless, at an average thickness of 110 μm , when determined by an

optical microscope (Fig.7), the membrane worked excellently with a displacement of about 5 mm, as depicted in Fig.6. The membrane with a dimension of 60 (l) x 30 (w) x 0.11 (t) is therefore used for stress analysis.



(a)



(b)

Fig.6. An application model of the CS/PVA membrane to cover the wound in a straight position (a) and in a bent position in which the displacement occurred.

The stress analysis of the membrane performed using Abaqus Simulia software shows the geometrically based-simulation result (Fig.8) and von mises stress of the membranes when the elbow of a hand is folded. It is shown that the maximum von mises of the membrane is about 7.67 MPa, which is equivalent to the maximum tensile strength, and the displacement demonstrates a maximum value of around 5 mm, which corresponds to the actual measurement exhibited in Fig.6b.

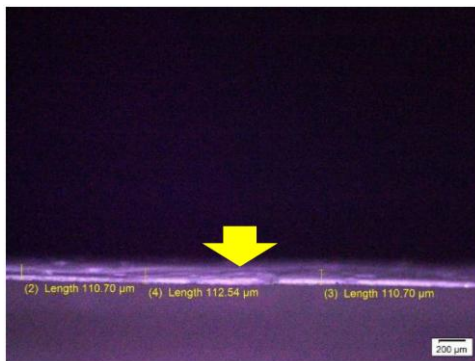


Fig.7. An optical micrograph of a cross-section of the membrane showing an average thickness.

This result suggested that the CS/PVA membrane with a CS/PVA ratio of 20/80 would be useful for an

alternative wound dressing material by designing a dimension of 60 mm in length, 30 mm in width and a minimum thickness of 0.11 mm (110 μm) which provides a 5 mm displacement of the membrane. However, a significant improvement in the tensile properties of the nanofibrous membrane is required in the next research.

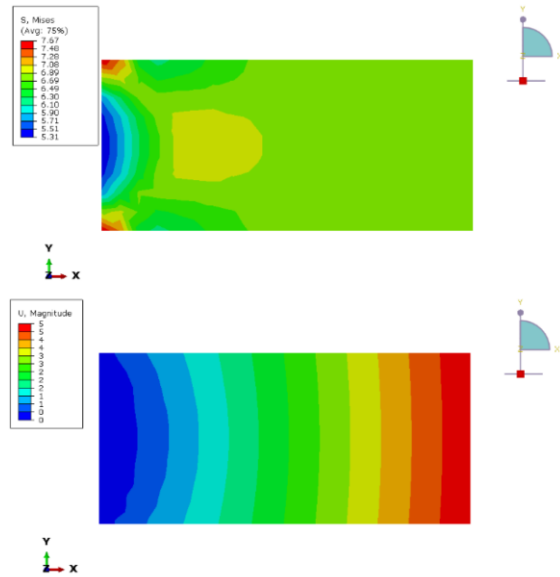


Fig.8. Abaqus Simulia simulation result.

IV. CONCLUSION

The electrospinning technique has successfully manufactured the CS/PVA nanofibrous membranes. The influence of the variation of CS concentrations and CS/PVA ratio on the tensile properties of CS/PVA membranes has resulted in some significant points. Increased CS concentration increases the tensile strength of the CS/PVA membrane with a CS/PVA ratio of 5/95, resulting in an optimum CS concentration of 3% with a tensile strength of 5.62 ± 0.47 MPa. Various CS/PVA ratios at 3% CS concentration showed a gradual increase in the tensile strength and modulus in which the maximum values reached by the membrane with CS/PVA ratio of 20/80 were 7.68 ± 1.94 MPa and 46.3 ± 2.89 MPa, respectively, and the elongation at break of 118.65 ± 10 %. Based on the simulation result using FEM supported by Abaqus Simulia software, the CS/PVA membrane with those properties is recommended as a wound dressing material by designing a dimension of 60 mm in length, 30 mm in width, and a minimum thickness of 0.11 mm (110 μm).

ACKNOWLEDGMENTS

This work was supported by a research grant of "Penelitian Dasar Unggulan Perguruan Tinggi", contract no: 227/SP2H/LT/DRPM/2019 by the Directorate General of Higher Education (DIKTI), Ministry of Research, Technology and Higher

Education, the Republic of Indonesia. The authors would like to thank Mr Kunto Wandono for his assistance related to the modification of the electro spinning machine.

REFERENCES

- [1] S. Islam, M. Khan, and A. N. Alam, "Production of chitin and chitosan from shrimp shell wastes," *J. Bangladesh Agric. Univ.*, vol. 14, no. 2, pp. 253–259, 2017.
- [2] L. D. Tolesa, B. S. Gupta, and M. J. Lee, "Chitin and chitosan production from shrimp shells using ammonium-based ionic liquids," *Int. J. Biol. Macromol.*, vol. 130, pp. 818–826, 2019.
- [3] M. Yadav, P. Goswami, K. Paritosh, M. Kumar, N. Pareek, and V. Vivekanand, "Seafood waste: a source for preparation of commercially employable chitin/chitosan materials," *Bioresour. Bioprocess.*, vol. 6, no. 1, pp. 8–28, 2019.
- [4] M. Rodríguez-Vázquez, B. Vega-Ruiz, R. Ramos-Zúñiga, D. A. Saldaña-Koppel, and L. F. Quiñones-Olvera, "Chitosan and Its Potential Use as a Scaffold for Tissue Engineering in Regenerative Medicine," *Biomed Res. Int.*, vol. 2015, pp. 1–15, 2015.
- [5] D. Zhao, S. Yu, B. Sun, S. Gao, S. Guo, and K. Zhao, "Biomedical applications of chitosan and its derivative nanoparticles," in *Polymers*, vol. 10, no. 4, pp. 479, 2018.
- [6] T. J. Gutiérrez, *Chitosan Applications for the Food Industry*, DOI: 10.1002/9781119364849, Chapter 8, 2017.
- [7] H. Wang, J. Qian, and F. Ding, "Emerging Chitosan-Based Films for Food Packaging Applications," *J. Agric. Food Chem.*, vol. 66, no. 2, pp. 395–413, 2018.
- [8] J. A. Vázquez, I. Rodríguez-Amado, M. I. Montemayor, J. Fraguas, M. P. Del González, and M. A. Murado, "Chondroitin sulfate, hyaluronic acid and chitin/chitosan production using marine waste sources: Characteristics, applications and eco-friendly processes: A review," *Mar. Drugs*, vol. 11, no. 3, pp. 747–774, 2013.
- [9] Q. X. Wu, D. Q. Lin, and S. J. Yao, "Design of chitosan and its water soluble derivatives-based drug carriers with polyelectrolyte complexes," *Mar. Drugs*, vol. 12, no. 12, pp. 6236–6253, 2014.
- [10] C. Brough, D. A. Miller, J. M. Keen, S. A. Kucera, D. Lubda, and R. O. Williams, "Use of Polyvinyl Alcohol as a Solubility-Enhancing Polymer for Poorly Water Soluble Drug Delivery (Part 1)," *AAPS PharmSciTech*, vol. 17, no. 1, pp. 167–179, 2016.
- [11] E. Biazar et al., "Design of Electrospun Poly vinyl alcohol/Chitosan Scaffold and Its Cellular Study," *J. Paramed. Sci.*, vol. 6, no. 3, pp. 46–51, 2015.
- [12] K. P. Chellamani, P. Sundaramoorthy, and T. Suresham, "Wound dressing made out of Poly Vinyl Alcohol/Chitosan nanomembranes," *J. Acad. Indus. Res.*, vol. 1, no. 6, p. 342–347, 2012.
- [13] M. Wang, A. K. Roy, and T. J. Webster, "Development of chitosan/poly(vinyl alcohol) electrospun nanofibers for infection related wound healing," *Front. Physiol.*, vol. 7, pp. 2016–2018, 2017.
- [14] S. Ahmadi Majd, M. Rabbani Khorasgani, S. J. Moshtaghian, A. Talebi, and M. Khezri, "Application of Chitosan/PVA Nano fiber as a potential wound dressing for streptozotocin-induced diabetic rats," *Int. J. Biol. Macromol.*, vol. 92, pp. 1162–1168, 2016.
- [15] R. P. Gonçalves, W. H. Ferreira, R. F. Gouvêa, and C. T. Andrade, "Effect of chitosan on the properties of electrospun fibers from mixed poly(Vinyl Alcohol)/Chitosan solutions," *Mater. Res.*, vol. 20, no. 4, pp. 984–993, 2017.
- [16] D. I. Sanchez-Alvarado, J. Guzmán-Pantoja, U. Páramo-García, A. Maciel-Cerda, R. D. Martínez-Orozco, and R. Vera-Graziano, "Morphological study of chitosan/poly (vinyl alcohol) nanofibers prepared by electrospinning, collected on reticulated vitreous carbon," *Int. J. Mol. Sci.*, vol. 19, no. 6, pp. 1–12, 2018.
- [17] Z. Norouzi, M. Abdouss, A. Tajiki, S. M. Rezaei, and M. K. Nahooji, "Application of chitosan/PVA nanofibrous composite for molecular capture," vol. 7, no. 3, pp. 221–226, 2018.
- [18] M. A. Abureesh, A. A. Oladipo, and M. Gazi, "Facile synthesis of glucose-sensitive chitosan–poly(vinyl alcohol) hydrogel: Drug release optimization and swelling properties," *Int. J. Biol. Macromol.*, vol. 90, pp. 75–80, 2016.
- [19] M. Koosha and H. Mirzadeh, "Electrospinning, mechanical properties, and cell behavior study of chitosan/PVA nanofibers," *J. Biomed. Mater. Res. - Part A*, vol. 103, no. 9, pp. 3081–3093, 2015.
- [20] C. Lustriane, F. M. Dwivany, V. Suendo, and M. Reza, "Effect of chitosan and chitosan-nanoparticles on post harvest quality of banana fruits," *J. Plant Biotechnol.*, vol. 45, no. 1, pp. 36–44, 2018.
- [21] A. Islam, T. Yasin, M.A. Rafiq, T.H. Shah, A. Sabir, S.M. Khan, and T. Jamil, "In-situ crosslinked nanofiber mats of chitosan/poly(vinyl alcohol) blend: Fabrication, characterization and MTT assay with cancerous bone cells," *Fibers Polym.*, vol. 16, no. 9, pp. 1853–1860, 2015.
- [22] S. Huan, G. Liu, G. Han, W. Cheng, Z. Fu, Q. Wu, and Q. Wang et al., "Effect of experimental parameters on morphological, mechanical and hydrophobic properties of electrospun polystyrene fibers," *Materials*, vol. 8, no. 5, pp. 2718–2734, 2015.
- [23] Z. Cui, Z. Zheng, L. Lin, J. Si, Q. Wang, X. Peng, and W. Chen, "Electrospinning and crosslinking of polyvinyl alcohol / chitosan composite nanofiber for transdermal drug delivery," vol. 37, no. 6, pp. 1917–1928, 2018.