

# **Sustainable Civil Infrastructures**

## **Editor-in-chief**

Hany Farouk Shehata, Cairo, Egypt

## **Advisory Board**

Dar-Hao Chen, Texas, USA

Khalid M. El-Zahaby, Giza, Egypt

### *About this Series*

Sustainable Infrastructure impacts our well-being and day-to-day lives. The infrastructures we are building today will shape our lives tomorrow. The complex and diverse nature of the impacts due to weather extremes on transportation and civil infrastructures can be seen in our roadways, bridges, and buildings. Extreme summer temperatures, droughts, flash floods, and rising numbers of freeze-thaw cycles pose challenges for civil infrastructure and can endanger public safety. We constantly hear how civil infrastructures need constant attention, preservation, and upgrading. Such improvements and developments would obviously benefit from our desired book series that provide sustainable engineering materials and designs. The economic impact is huge and much research has been conducted worldwide. The future holds many opportunities, not only for researchers in a given country, but also for the worldwide field engineers who apply and implement these technologies. We believe that no approach can succeed if it does not unite the efforts of various engineering disciplines from all over the world under one umbrella to offer a beacon of modern solutions to the global infrastructure. Experts from the various engineering disciplines around the globe will participate in this series, including: Geotechnical, Geological, Geoscience, Petroleum, Structural, Transportation, Bridge, Infrastructure, Energy, Architectural, Chemical and Materials, and other related Engineering disciplines.

More information about this series at <http://www.springer.com/series/15140>

Louay Mohammad  
Editor

# Advancement in the Design and Performance of Sustainable Asphalt Pavements

Proceedings of the 1st GeoMEast International  
Congress and Exhibition, Egypt 2017  
on Sustainable Civil Infrastructures

 Springer

*Editor*

Louay Mohammad  
Louisiana State University  
Baton Rouge, LA  
USA

ISSN 2366-3405

Sustainable Civil Infrastructures

ISBN 978-3-319-61907-1

DOI 10.1007/978-3-319-61908-8

ISSN 2366-3413 (electronic)

ISBN 978-3-319-61908-8 (eBook)

Library of Congress Control Number: 2017946469

© Springer International Publishing AG 2018

This work is subject to copyright. All rights are reserved by the Publisher, whether the whole or part of the material is concerned, specifically the rights of translation, reprinting, reuse of illustrations, recitation, broadcasting, reproduction on microfilms or in any other physical way, and transmission or information storage and retrieval, electronic adaptation, computer software, or by similar or dissimilar methodology now known or hereafter developed.

The use of general descriptive names, registered names, trademarks, service marks, etc. in this publication does not imply, even in the absence of a specific statement, that such names are exempt from the relevant protective laws and regulations and therefore free for general use.

The publisher, the authors and the editors are safe to assume that the advice and information in this book are believed to be true and accurate at the date of publication. Neither the publisher nor the authors or the editors give a warranty, express or implied, with respect to the material contained herein or for any errors or omissions that may have been made. The publisher remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.

Printed on acid-free paper

This Springer imprint is published by Springer Nature

The registered company is Springer International Publishing AG

The registered company address is: Gewerbestrasse 11, 6330 Cham, Switzerland

# Preface

Toward building sustainable and longer civil infrastructures, the engineering community around the globe continues undertaking research and development to improve existing design, modeling, and analytical capability. Such initiatives are also the core mission of the Soil-Structure Interaction Group in Egypt (SSIGE) to contribute to the ongoing research toward sustainable infrastructure. This conference series “GeoMEast International Congress and Exhibition” is one of these initiatives.

Ancient peoples built their structures to withstand the test of time. If we think in the same way, our current projects will be a heritage for future generations. In this context, an urgent need has quickly motivated the SSIGE and its friends around the globe to start a new congress series that can bring together researchers and practitioners to pursue “Sustainable Civil Infrastructures.” The GeoMEast 2017 is a unique forum in the Middle East and Africa that transfers from the innovation in research into the practical wisdom to serve directly the practitioners of the industry.

More than eight hundred abstracts were received for the first edition of this conference series “GeoMEast 2017” in response to the Call for Papers. The abstracts were reviewed by the Organizing and Scientific Committees. All papers were reviewed following the same procedure and at the same technical standards of practice of the TRB, ASCE, ICE, ISSMGE, IGS, IAEG, DFI, ISAP, ISCP, ITA, ISHMII, PDCA, IUGS, ICC, and other professional organizations who have supported the technical program of the GeoMEast 2017. All papers received a minimum of two full reviews coordinated by various tracks’ chairs and supervised by the volumes editors through the Editorial Manager of the SUCI “Sustainable Civil Infrastructure” book series. As a result, 15 volumes have been formed of the final +320 accepted papers. The authors of the accepted papers have addressed all the comments of the reviewers to the satisfaction of the tracks’ chairs, the volumes editors, and the proceedings editor. It is hoped that readers of this proceedings of the GeoMEast 2017 will be stimulated and inspired by the wide range of papers written by a distinguished group of national and international authors.

Publication of this quality of technical papers would not have been possible without the dedication and professionalism of the anonymous papers reviewers. The names of these reviewers appear in the acknowledgment that follows. For any additional reviewers whose names were inadvertently missed, we offer our sincere apologies.

We are thankful to Dr. Hany Farouk Shehata, Dr. Nabil Khelifi, Dr. Khalid M. ElZahaby, Dr. Mohamed F. Shehata, and to all the distinguished volumes' editors of the proceedings of the GeoMEast 2017. Appreciation is extended to the authors and tracks' chairs for their significant contributions. Thanks are also extended to Springer for their coordination and enthusiastic support to this conference. The conference staff acknowledges the assistance of Ms. Janet Sterritt-Brunner, Mr. Arulmurugan Venkatasalam in the final production of the 15 edited volumes "Proceedings of GeoMEast 2017".

# Contents

<b>Development and Finite Element Analysis of Piezoelectric-Based Prototypes for Harvesting Energy from Roadway Pavement.</b> . . . . .	1
Hossein Roshani, Samer Dessouky, Arturo Montoya, A.T. Papagiannakis, and Ala Abbas	
<b>A Bitumen-Based Prototype to Predict the Workability of Asphalt Concrete Mixtures.</b> . . . . .	14
Aboelkasim Diab and Zhanping You	
<b>The Use of Wastewater in Construction of Base Course Layers in Pavement Structures.</b> . . . . .	31
Farid H. Abed, Munir D. Nazzal, Mousa F. Attom, Magdi E. El-Emam, Nouran ElMessalami, and Saif Al-Dabagh	
<b>Hydraulic Conductivity of Layered Compacted Granular Materials Used as Pavement Foundation.</b> . . . . .	38
Namir K.S. Al-Saoudi and Khawla H.H. Shubber	
<b>Extending the Service Life of Bridges Through Proper Compaction of Asphalt Decks.</b> . . . . .	49
Amir Abd El Halim, Ahmed El-Desouky, and Abd El Halim	
<b>Characteristics of Jointed Rigid Airfield Pavement Using Different Material Parameters and Modeling Techniques.</b> . . . . .	66
Ahmed E. Abu El-Maaty, Ghada M. Hekal, Eman M. Salah El-Din, and Saad El-Hamrawy	
<b>Effect of Construction Induced Cracks on Tensile Strength and Bonding Between Asphalt Concrete Layers of Pavement Under Different Temperatures.</b> . . . . .	85
Graziela Girardi, Mohammad Ramezani, and A.O. Abd El Halim	

<b>Effect of Wet-Dry Cycle on Durability of Cement-Stabilized Recycled Pavement Base Aggregates</b> . . . . .	98
Saif Bin Salah, Sahadat Hossain, Mohammad Faysal, Mohammad Sadik Khan, and Carla Maria Flores	
<b>Full Depth Reclamation (FDR) to Repair Road Damaged in the Energy Sector</b> . . . . .	115
Dar Hao Chen, Tom Scullion, and Kun Li	
<b>Prediction of Strength and Stiffness Properties of Recycled Pavement Base Materials Using Non-destructive Impact Echo Test</b> . . . . .	121
Masrur Mahedi, Sahadat Hossain, Mohammad Faysal, Mohammad Sadik Khan, and Asif Ahmed	
<b>Predicting Performance of Flexible Pavement Using Finite Element Method</b> . . . . .	137
Anand B. Tapase and M.S. Ranadive	
<b>Implementation Initiatives of the Mechanistic-Empirical Pavement Design Guide in Countries with Insufficient Design Input Data – The Case of Lebanon</b> . . . . .	147
Ghassan R. Chehab, Rana Hajj Chehade, Lamis Houssami, and Rayane Mrad	
<b>Structural Evaluation of Flexible Pavement Using Non-destructive Techniques in Low Volume Road</b> . . . . .	168
Vinod Kumar, Sunny Deol, and Rakesh Kumar	
<b>Application of Artificial Neural Networks for Hot Mix Asphalt Dynamic Modulus (E*) Prediction</b> . . . . .	185
Sherif El-Badawy and Ragaa Abd El-Hakim	
<b>Potentials for Using Mechanically Activated Concrete Powder in Stabilized Granular Pavement Mixtures</b> . . . . .	203
Jan Valentin, George Karráa, Jan Suda, Jakub Šedina, Pavel Tesárek, and Zdeněk Prošek	
<b>Pavement Modification Using Enzymatic Lime</b> . . . . .	221
Greeshma Nizy Eujine, S. Chandrakaran, and N. Sankar	
<b>Numerical Modeling of Heat Production for a Snow-Melting System Using Geothermal Energy in North Dakota</b> . . . . .	232
I-Hsuan Ho	
<b>Assessment of Interlayer Bonding Properties with Static and Dynamic Devices</b> . . . . .	244
Christiane Raab, Elise Fourquet, Omar Abd El Halim, and Manfred N. Partl	



**Wavelet-Spectrogram Analysis of Surface Wave Technique for Quick NDT Measurement on Surface Layer of Pavement** . . . . . 256  
Sri Atmaja P. Rosyidi

**Thermal Energy Harvesting from Asphalt Roadway Pavement** . . . . . 272  
Utpal Datta, Samer Dessouky, and A.T. Papagiannakis

**Monitoring the Impact of Micro Cracks Healing Cycles on the Deformation of Asphalt Concrete Under Repeated Loading** . . . . . 287  
Saad Issa Sarsam and Hanan Kadim Husain

**A State-of-the-Art Review of Different Conditions Influencing the Behavioral Aspects of Flexible Pavement** . . . . . 300  
Piyush G. Chandak, Anand B. Tapase, Sabir S. Sayyed, and Abdulrashid C. Attar

**Performance Testing of Paving Mixes for Libya’s Hot and Arid Conditions, Using Marshall Stability and SUPERPAVE Gyrotory Compactor Methods** . . . . . 313  
Fathi S. Almadwi and Gabriel J. Assaf

**Author Index** . . . . . 325

# Wavelet-Spectrogram Analysis of Surface Wave Technique for Quick NDT Measurement on Surface Layer of Pavement

Sri Atmaja P. Rosyidi<sup>(✉)</sup>

Department of Civil Engineering, Universitas Muhammadiyah Yogyakarta,  
Yogyakarta, Indonesia  
atmaja\_sri@umy.ac.id

**Abstract.** Reliable assessment of in situ pavements stiffness is an important aspect in effectively managing a pavement system. The aim of this paper is to propose the new procedure, namely the wavelet-spectrogram of surface wave (WSSW) technique for non-destructively measurement of elastic modulus on surface layer of a pavement system. Using two receivers, surface wave propagation on pavement surface was recorded and transformed into in frequency domain by wavelet analysis. For this analysis, a derivative Gaussian wavelet was selected as an appropriate mother wavelet for seismic waveform propagating along pavement surface. Thus, an interactive 2-D plot of time-frequency spectrogram consisting of wave-energy spectrum was simultaneously generated. CWT-filtration method was implemented in order to reduce the effect of noisy signal recorded during measurement. From selected wave spectrogram, the unwrapped phase different spectrum was generated to obtain phase velocity which was performed by least-square linear regression. Finally, the elastic modulus of pavement surface layer was calculated from a modified relationship between phase velocity, Poisson ratio and density of pavement surface layer. The results show that the proposed technique is able to measure in situ elastic stiffness of the surface layer. In addition, the change of the surface layer stiffness is also able to be monitored. The stiffness (elastic modulus) produced by the WSSW technique is classified as a modulus at very low strain level.

## 1 Introduction

The spectral-analysis-of-surface-wave (SASW) is a well-known of non-destructive techniques (NDT) in pavement evaluation and geotechnical investigation. The SASW employs the surface waves dispersion in order to determine the shear wave velocity corresponding to stiffness of each layer at pavement and soil profile. The method performs three steps of an elaborated data process, i.e., (1) collecting seismic data, (2) constructing an experimental dispersion curve and (3) conducting an inversion process of the dispersion curve for generating a stiffness profile. The method has been improved and utilized in many civil engineering applications, e.g., site characterization (Stokoe et al. 1994), soil density (Kim et al. 2001), pavement characterization (Rosyidi et al. 2007, Yusoff et al. 2015), soil damping measurement in soft soil sites (Rosyidi and Taha 2012), and asphaltic pavement measurement (Hazra and Kumar 2014, Rosyidi 2015).

In inversion process, the advanced mathematical approach is required to produce the stiffness profile from a dispersion curve. Reliable inversion procedure using stress-wave propagation theories, i.e., the transfer matrix method, the dynamic stiffness matrix method and the finite difference method should be employed. All the methods require an initial profile model consists of a set of homogeneous layers extending to infinity in the horizontal direction. In each layer of profile, the information such as a thickness, a shear wave velocity, a Poisson's ratio (or compression wave velocity), and a mass density are assigned. Based on the initial profile, a theoretical dispersion curve is calculated using one of these wave propagation theories. The theoretical dispersion curve is then compared with the experimental dispersion curve. If the two dispersion curves do not match, the initial profile (number of layers, layer thickness, shear wave velocity, or any combination) is adjusted, and another theoretical dispersion curve is calculated. The trial-and-error procedure is repeated until the two curves match, and then the associated assumed profile is considered the real profile. In addition, when the SASW method is performed on irregular stiffness profile, i.e., pavement structure, the trial-and-error procedure becomes a difficult analysis and takes longer time in data processing. Moreover, several researchers have reported on difficulties related to surface wave measurements at pavement sites. Most of these difficulties are reported to originate from the influence of higher modes of propagation (Al-Hunaidi 1992, Tokimatsu et al. 1992, Ganji et al. 1998; Ryden et al. 2004).

The seismic surface wave method is not able to separate different modes of propagation on a pavement system and thus measures a superposition of all propagating waves at the specific receiver locations. This superposed effect, often termed apparent phase velocity or pseudophase velocity, changes with distance and has forced the evaluation of the data to take into account the position of the receivers and the superposition of different modes for the inversion of experimental dispersion curves. Ryden et al. (2004) proposed a new approach in seismic pavement testing where the different modes of propagation are separated, thereby potentially clarifying some of the noted difficulties with the SASW method applied to pavement testing. Their approach is based on the multichannel analysis of surface wave (MASW) data processing technique. However, due to complexity in surface wave analysis, application of these methods on pavement evaluation is still relatively limited. On the other hand, in pavement evaluation system, the need of accurate, cost-effective and non-destructive evaluation is becoming ever important because the rehabilitation and management of roads is becoming increasingly difficult due to the increasing number of aging roads and limited budgets. As well, for practical purpose, pavement engineer usually needs a quick and relatively effortless analysis for determining the structural condition of pavement surface layers.

In this paper, a new procedure in a surface wave technique which is using continuous wavelet transform combined with the elastic stiffness formulation for obtaining the phase velocity is introduced. This method is namely the wavelet-spectrogram of surface wave (WSSW) technique. The time-frequency decomposition of continuous wavelet transform (CWT) on seismic signals is employed to characterize the phase information of phase different spectrum. It provides a reliable information of wave spectrum in the pavement profile. An algorithm on phase different calculation in this analysis aims to avoid the use of a complex inversion algorithm to obtain the elastic

modulus of the pavement surface layer. In the SASW method, data analysis and processing in frequency domain has been carried out by fast Fourier transforms (FFT). However, due to Fourier transform works by expressing any arbitrary periodic function of time with period as sum a set of sinusoidal, this analysis becomes inconsistent and is unable to preserve the time dependence and describe the evolutionary spectral characteristics of non-stationary processes (Rosyidi et al. 2009). Wavelet analysis is becoming an effective tool for analyzing localized variations of power within a time series. By decomposing a time series into time-frequency spectrum (TFW), one is able to determine both the dominant modes of variability and how those modes vary in time. A typical result from a case study is presented herein for the structural assessment of an existing asphalt concrete (AC) pavement in Purwakarta, West Java, Indonesia.

### 1.1 Continuous Wavelet Transform

The continuous wavelet transform (CWT) has been used in many studies in geophysics (Foufoula-Georgiou and Kumar 1995) and civil engineering application (Rosyidi et al. 2009). The continuous wavelet transform (CWT) technique is an alternative tool for localizing the interested frequency of seismic signal processing particularly in non-stationary problems. Wavelets dilate in such a way that the time support changes for different frequency. When the time support increases or decreases, the frequency support of the wavelet is shifted toward high or low frequencies, respectively. Therefore, as the frequency resolution increases, the time resolution decreases and vice versa. The characteristic of time-frequency resolution creates the CWT technique useful for non-stationary seismic analysis.

A wavelet is defined as a function of  $\psi(t) \in L^2(\mathfrak{R})$  with a zero mean, which is localized in both time and frequency. By dilating and translating the wavelet  $\psi(t)$ , it can be used to produce a family of wavelets as:

$$\psi_{\sigma,\tau}(t) = \frac{1}{\sqrt{\sigma}} \psi\left(\frac{t-\tau}{\sigma}\right) \quad (1)$$

where  $\sigma$  is the dilation parameter or scale and  $\tau$  is the translation parameter ( $\sigma, \tau \in \mathfrak{R}$  and  $\sigma \neq 0$ ). The wavelet has also various wavelet shape used for signal analysis which is called the mother of wavelet, i.e., Gaussian, Morlet, Paul and Mexican Hat. An appropriate selection of wavelet shape signal analysis depends on the seismic waveforms.

The CWT is defined as the inner product of the family wavelets  $\Psi_{\sigma,\tau}(t)$  with the signal of  $f(t)$  which is given as:

$$F_W(\sigma, \tau) = \langle f(t), \psi_{\sigma,\tau}(t) \rangle = \int_{-\infty}^{\infty} f(t) \frac{1}{\sqrt{\sigma}} \bar{\psi}\left(\frac{t-\tau}{\sigma}\right) dt \quad (2)$$

where  $\bar{\psi}$  is the complex conjugate of  $\psi$ ,  $F_W(\sigma, \tau)$  is the time-scale map.

In this study, the mother wavelet of the Gaussian Derivative (GoD) was used. The real component of the GoD wavelet in the time and frequency domains is defined as follows:

$$\psi_0(t) = \frac{(-1)^{m+1}}{\sqrt{\Gamma(m + \frac{1}{2})}} \frac{d^m}{d\eta^m} \left( e^{-t^2/2} \right) \quad (3)$$

$$\hat{\psi}_0(s\omega) = -\frac{i^m}{\sqrt{\Gamma(m + \frac{1}{2})}} (s\omega)^m \left( e^{-(s\omega)^2/2} \right) \quad (4)$$

where  $m$  is the wave number and  $\Gamma$  is the Gamma function. The complex wavelet is generated by the addition of a Heaviside function in the frequency domain. This wavelet decays with the square root of the gamma function. The GoD has wavelet's derivative order that can be varied in order to get the best resolution of the waveform.

## 2 Research Method

### 2.1 Field Measurement

In field measurement of the WSSW method, a set of ball bearing with weight from 5 to 15 g was used as an impact source to generate seismic waves on the surface layer of pavement. Generated seismic waves were then detected using two high frequency accelerometers. Consequently, the signals were recorded using an ADT analog-digital acquisition connected to a notebook computer for post processing (Fig. 1). In this study, two configurations of mid-point receiver spacing and the receiver-source spacings were employed in order to sample different depths of pavement surface. The configuration of mid-point receiver spacings was described in Fig. 2. The receiver spacing ( $d_2$ ) was obtained as a distance which the length is less than and/or equal to the thickness ( $H$ ) of pavement surface layer. Whereas, the distance between a source and first receiver ( $d_1$ ) was set as equal to receivers spacing ( $d_2$ ). Due to the interested pavement area in measurement was asphaltic surface layer, the short receiver spacings of 5, 10 and 15 cm with a high frequency source were only used. In the test, repetition procedure (forward and backward) until at least 4 to 6 times in each receiver spacing measurement should be employed in order to minimize the effect of internal phase shift between receivers and to enhance a good average of received signals.

Beside the WSSW test, the SASW measurement was also carried out at same sites of existing road pavement in Purwakarta, West Java, Indonesia. The pit test was also conducted to acquire the information of a pavement profile. From the pit test, the pavement structure consists of an asphalt concrete (AC) layer (18 cm), crushed stone of base course (10 cm), sub-base course (30 cm) over a subgrade layer.

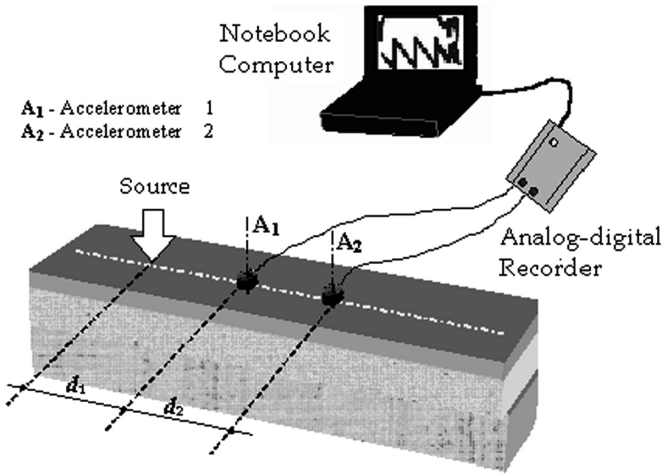


Fig. 1. Experimental set up of WSSW measurement on a pavement structure

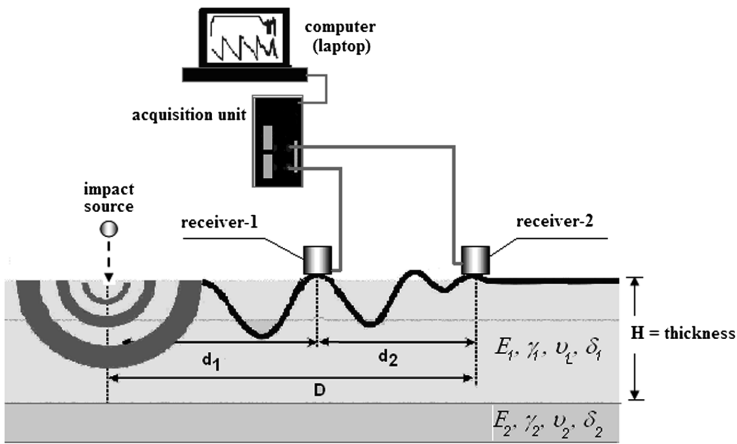


Fig. 2. Mid-point receivers configuration of WSSW measurement on pavement structure

## 2.2 Data Analysis and Process

A proposed procedure of the WSSW method consists of seismic data analysis using continuous wavelet transform and elastic modulus calculation of elastic linear model on pavement surface layer which is described as follows:

1. The seismic wave data are collected from field measurement using a configuration of the mid-point receiver spacings.
2. The time-frequency spectrum analysis based on continuous wavelet transform of Gaussian Derivative (DoG) mother wavelet is carried out for two signal waveforms recorded from field measurement. By decomposing a time series of seismic

waveform into time-frequency (TF) spectrogram, the dominant modes of variability and how those modes vary in time can be determined very well.

- Phase information of the transfer function (phase spectrum) are then determined from both TF spectrograms. The data informs the time difference of wave propagating from first to second receiver. A mathematical expression for calculating phase spectrum from TF spectrogram is defined by (Rosyidi and Taha 2012):

$$H(f) = \frac{Y(f)}{X(f)} \approx \frac{W_{f(u,s)}^Y}{W_{f(u,s)}^X} = \frac{\int_{-\infty}^{\infty} Y(t) \frac{1}{\sqrt{\sigma}} \psi * \left(\frac{t-\tau}{\sigma}\right) dt}{\int_{-\infty}^{\infty} X(t) \frac{1}{\sqrt{\sigma}} \psi * \left(\frac{t-\tau}{\sigma}\right) dt} \tag{5}$$

where,

$X(f)$  = spectrum input of signal,  $X(t)$ , from first receiver,

$Y(f)$  = spectrum output of signal,  $Y(t)$ , from second receiver,

$$W_{f(u,s)}^Y = \int_{-\infty}^{\infty} Y(t) \frac{1}{\sqrt{s}} g\left(\frac{t-u}{s}\right) e^{-i\zeta(t-u)} dt \tag{6}$$

$$W_{f(u,s)}^X = \int_{-\infty}^{\infty} X(t) \frac{1}{\sqrt{s}} g\left(\frac{t-u}{s}\right) e^{-i\zeta(t-u)} dt \tag{7}$$

From Eq. 7, the phase spectrogram in time-frequency domain can be obtained by:

$$H(u, s) = \frac{W_f^{XY}(u, s)}{W_f^{XX}(u, s)} = \frac{|W_f^{XY}(u, s)| e^{i(\theta_Y(a,b) - \theta_X(a,b))}}{W_f^X(u, s)^* \times W_f^X(u, s)} \tag{8}$$

Thus, phase different is obtained from the ratio of the imaginary to real part of the phase spectrogram which is expressed as:

$$\phi = \tan^{-1} \left( \frac{\Im H(u, s)}{\Re H(u, s)} \right) \tag{9}$$

- The coherence function is used to visually inspect the quality of signals being recorded in the field and have a real value between zero and one in the range of frequencies being measured. The value of one indicates a high signal-to-noise ratio (i.e., perfect correlation between the two signals) while values of zero represents no correlation between the two signals. The coherence function is a ratio of the output power caused by the measured input to the total measured output which is defined as:

$$\gamma^2(f) = \frac{G_{yx}(f) \cdot G_{yx}^*(f)}{G_{xx}(f) \cdot G_{yy}(f)} \quad (10)$$

5. A linear relationship between the phase different and frequency from the transfer function spectrum is then derived. The phase velocity is examined as a function of distance from the slope value ( $m$ ). This relationship can be written as:

$$\phi = \left| \frac{360D}{V_{ph}} \right| f = mf \quad (11)$$

By Eq. 11, one can easily determine  $V_{ph}$  by performing a least-square linear regression over the frequency range in the transfer function spectrum and the slope of the best-fit line ( $m$ ) can be obtained. The phase velocity of surface wave propagation is independent of the wavelength for up to a wavelength approximately equal to thickness of the uppermost layer. The range of wavelength to be used can be estimated from the phase velocities ( $V_{ph}$ ) of the material anticipated at the site:

$$\lambda = \frac{V_{ph}}{f} \quad (12)$$

where  $f$  is the frequency.

6. If one simply generates high frequency waves and assumes that properties of the uppermost layer are uniform, the dynamic elastic moduli of the pavement materials can easily be determined as follows:

$$E = 2 \frac{\gamma}{g} V_S^2 (1 + \mu) = \frac{\gamma}{g} |KV_{ph}|^2 \quad (13)$$

$$K = (1.13 - 0.16\mu) \sqrt{\frac{2(1 - \mu)}{(1 - 2\mu)}} \quad (14)$$

where  $E$  is the dynamic elastic modulus, respectively,  $V_S$  is the shear wave velocity,  $V_{ph}$  is the phase wave velocity,  $g$  is the gravitational acceleration,  $\gamma$  is the total unit weight of the material and  $\mu$  is the Poisson's ratio.

## 3 Results and Discussion

### 3.1 Stiffness and Elastic Modulus

The WSSW measurements were carried out at 12 sites on existing asphalt pavements. A typical result of received signals from field measurement was shown in Fig. 3. The body waves (Primary and Secondary wave) and surface wave (Rayleigh wave) are clearly shown in both signal recordings. Therefore, the Gaussian Derivative (GoD) continuous wavelet transform (CWT) was employed on signals for generating a



time-frequency (TF) plot. Both CWT plots may overcome on identification problem of the spectral characteristics of non-stationary signals measured in two receivers. The typical CWT spectrogram for received signals with an improved time-frequency resolution is shown in Fig. 4. From Fig. 4, two main energy events at different frequency bands were also clearly detected which may result in both low and higher mode of seismic waves. It is able to observed that lower frequency energy was found in the range of 2.8–16 kHz in CWT spectrogram. This spectrum range is identified as surface wave signals. The level and frequency range of these signals were determined by independent-measurement of high level energy in surface wave propagation (up to 60% of total wave energy). Thus, the other energy event is identified as wave mode from direct and reflected body waves which was found in more than 20 kHz. The dominant wave energy found in CWT spectrogram at interested frequency range of surface waves can be clearly captured. The TF of GoD-CWT provides good resolutions at high frequencies of signals. It is also effective in the detection of frequency bandwidth of wave groups using various derivation order of this mother wavelet (GoD).



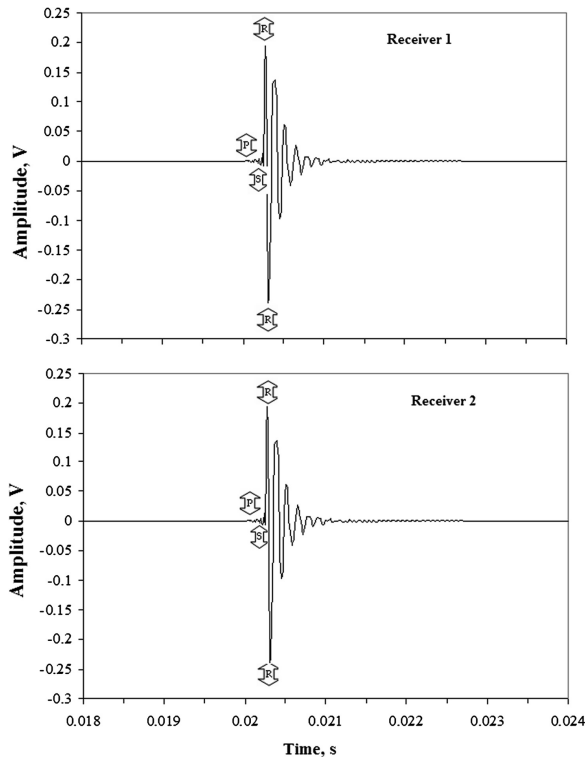


Fig. 3. Signal from WSSW measurement on a pavement structure

Based on both TF spectrograms (Fig. 4), the phase different between two signals for every wave frequency were then calculated. As a result, a transfer function spectrum on wrapped phase different curve was obtained as given in Fig. 5. The phase data

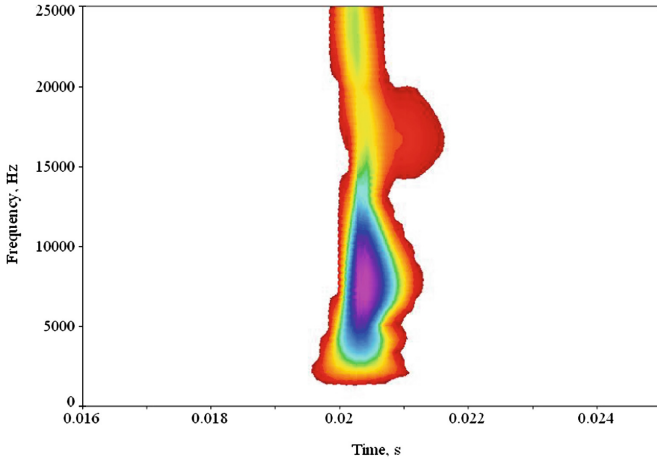

(a) CWT Spectrogram from receiver 1

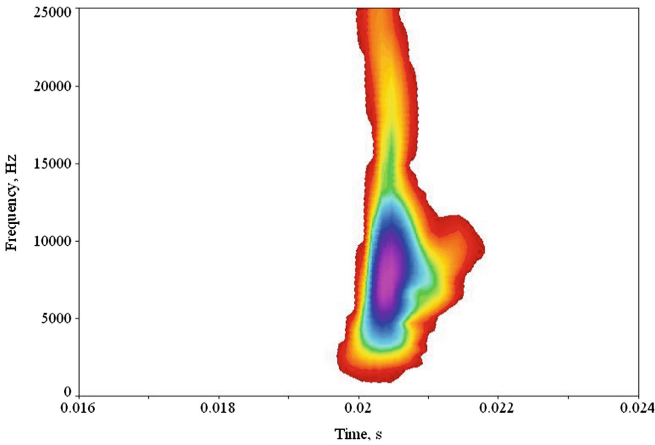


(b) CWT Spectrogram from receiver 2


**Fig. 4.** Time-frequency plot of received signals from measurement

oscillates between  $-\pi$  and  $\pi$  radian ( $-180$  and  $180$  degrees). This is the standard illustration of spectrum presenting phase data because the detail variation in data can be observed in a small space.

Figure 5 also shows that the phase different curve reveals a smooth trend of variation in phase with frequency up to a frequency of 25 kHz. It indicates the high-frequency surface waves were detected representing the high stiffness of the asphalt concrete surface layer on a pavement structure. The quality of phase data is also controlled by the coherence function. As shown in Fig. 6, the phase data up to frequency of 20 kHz have the value of coherence magnitude above 0.98.

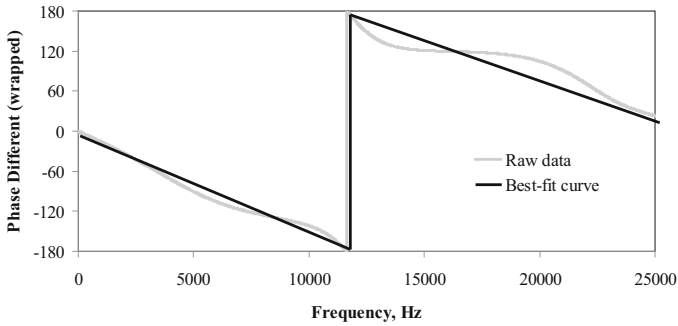


**Fig. 5.** Comparison between raw data and best-fit curve of wrapped transfer function spectrum from measurement

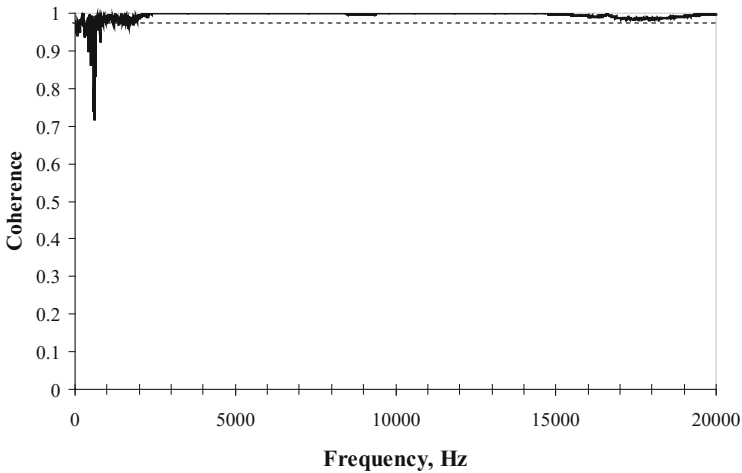

**Fig. 6.** Coherent function spectrum of received signals from measurement

In order to obtain the modulus value of the surface layer, the smoothed fitting process of weighing function was used. The fitted curve between the raw and the smoothed phase spectrum is shown in Fig. 5. Thus, the phase data is unwrapped by adding the number cycles to each phase. The unwrapped of the raw phase spectrum is also shown in Fig. 7. The unwrapped phase spectrum is smoothed by the linear regression as the best fit curve to the raw data. The slope of the line is more or less constant with frequency. A line is fitted to the curve in the range of the frequency corresponding to wavelengths shorter than the thickness of the surface layer. Slope value of the line can be used to determine the elastic modulus of the surface layer of the pavement profile using Eqs. 11, 13 and 14.

From Fig. 7, the slope ( $m$ ) of best-fit curve is found to be 0.0140. Consequently, the phase velocity can be calculated using Eq. 13 which is found to be 1028.57 m/s. Based on the phase velocity, field configuration data and material parameters, such as of

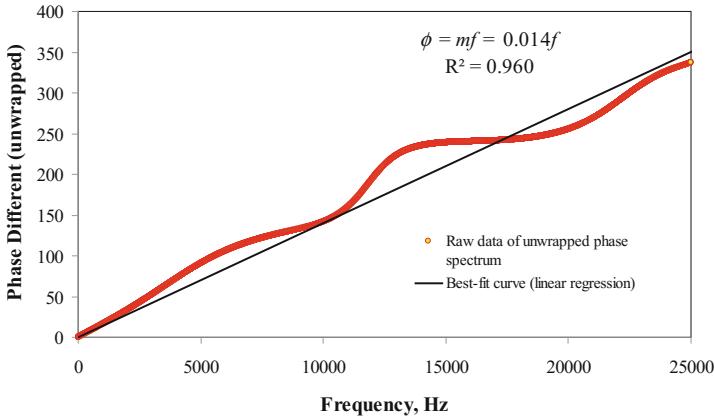


**Fig. 7.** Comparison between raw data and best-fit curve of unwrapped transfer function spectrum from measurement and slope analysis to obtain  $m$  value

receiver spacing ( $d_2$ ) of 5 cm, Poisson's ratio of asphaltic layer of 0.25 and unit weight for pavement material (AC) of 2,200 kg/m<sup>3</sup>, the elastic modulus of asphaltic (AC) surface layer is obtained as 845,662,040.80 kg/m<sup>2</sup> or 8456.62 MPa.


The result shows that the elastic modulus of AC layer can be easily determined using the WSSW technique. However, the value of elastic modulus presented is relatively high. It is due to the seismic technique measures the dynamic stiffness at very low strain level (less than 103%). In this level, the material modulus behavior can be assumed as a constant and have only a maximum value. To illustrate the usefulness and sensitivity of this approach in testing the surface layer, changes in the stiffness of the existing surface and the overlay layer of the pavement were measured in situ. Figure 8 shows that the different stiffness of an existing and overlay surface layer from the measured profile can be investigated well. Based on these results, it can be summarized that the stiffness changes in the surface layer were easily, non-destructively, and fast measured by the WSSW technique.

### 3.2 Validation with the SASW Method

In order to validate the results from the WSSW test, the spectral-analysis-of-surface-wave (SASW) analysis was conducted at same locations of a road pavement. In this method, a set of transient impact sources was used to generate surface wave energy that propagates horizontally near the surface layer of the pavement. The phase differences of signal data were obtained from the cross-power spectrum. Thus, the phase information was then unwrapped to produce the dispersion curve of the phase velocity versus wavelength. An inversion process was then iteratively employed to confirm the experimental dispersion curve from the theoretical model established. A 3-D stiffness matrix model (Rosyidi 2007) was employed in the SASW inversion analysis. Final stiffness profile was obtained after 16 times of iteration with the root-mean-square error (RMS) of 35.47 m/s or average deviation of about 5.92%.

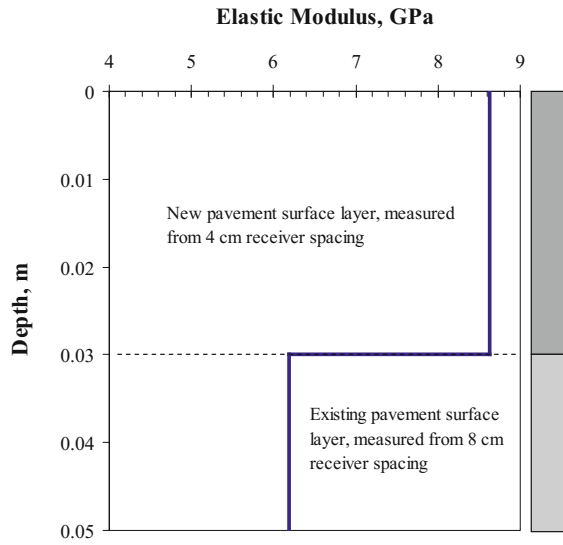


**Fig. 8.** Comparison between elastic modulus of an overlay and existing surface layer at pavement roads, Indonesia

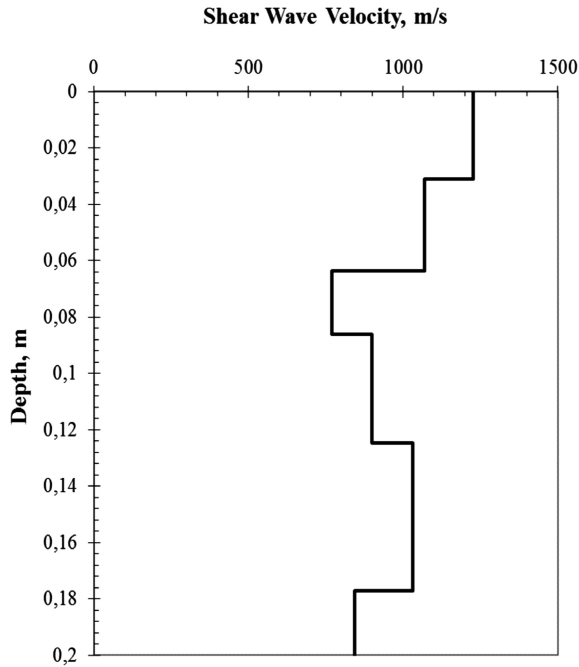

**Fig. 9.** The shear wave velocity profile from inversion of the experimental dispersion curve

The equivalent shear wave profile from the result of the inversion is shown in Fig. 9 and using the dynamic material equation, its equivalent dynamic elastic modulus profile is given in Fig. 10. A modulus profile as shown in Fig. 10 is only given to 10 cm depth of pavement structure due to the asphaltic layer was indicated at this level. A good agreement of elastic modulus resulted from the WSSW and the SASW method is also presented in Fig. 10. The result shows that the difference between both methods is calculated at 0.01% and 1.14% for first and second layer of pavement surface layer, respectively.

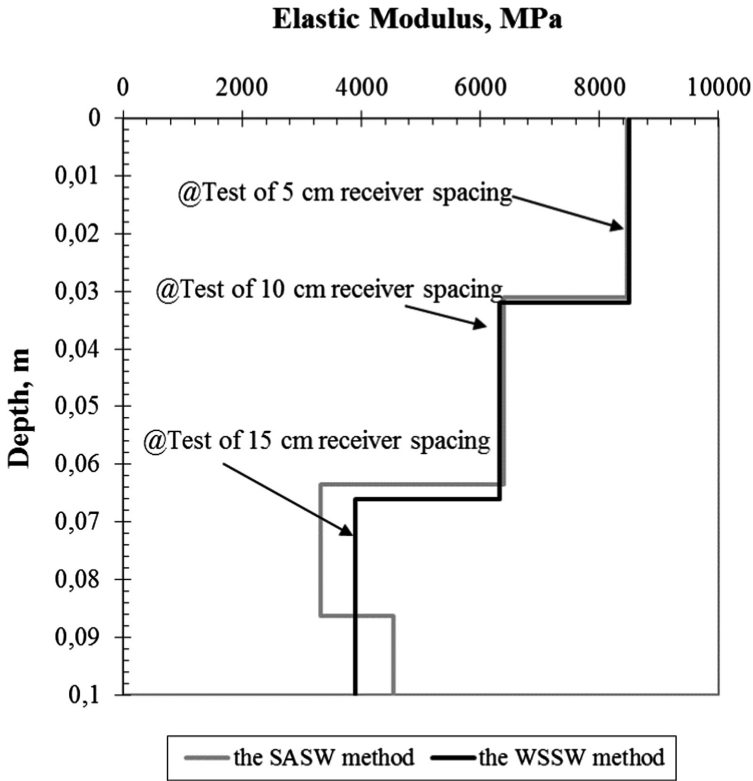

**Fig. 10.** The dynamic elastic modulus of the pavement profile from the SASW method and its comparison with the WSSW method

The falling weight deflectometer (FWD) method was also employed to validate the elastic modulus of pavement surface layer from the WSSW test. The elastic modulus of pavement surface layer obtained from both measurements is shown in Fig. 11. The elastic modulus obtained from the WSSW is higher comparison with value determined by the FWD. As mentioned earlier, the modulus measured at very low strain levels associated with surface wave method is in maximum value and it is independent from strain amplitude. In addition, the high frequency used in the seismic result in higher values of stiffness for pavement material. In the case of FWD, the modulus was measured at frequency of around 30 Hz (Fig. 12).

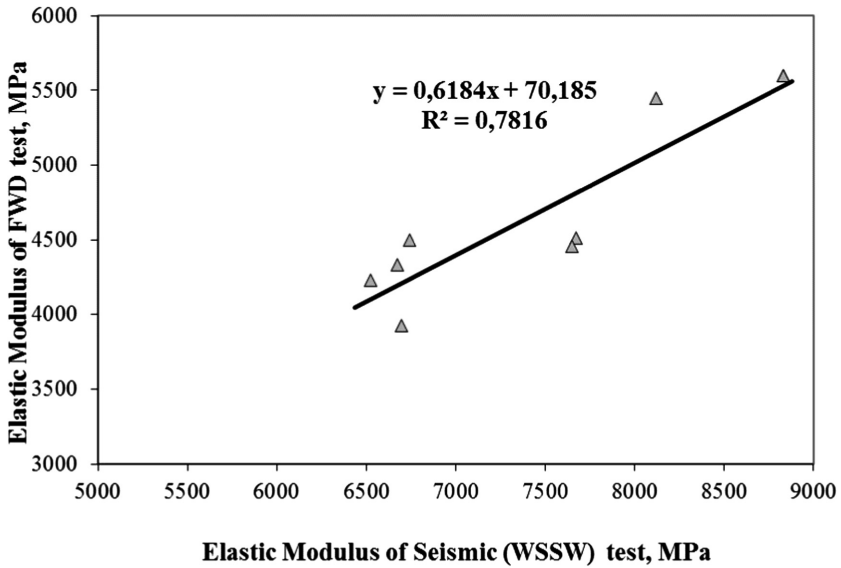


Fig. 11. Comparison elastic modulus of surface layers from the SASW test compared to the FWD test at Purwakarta State Road, Indonesia

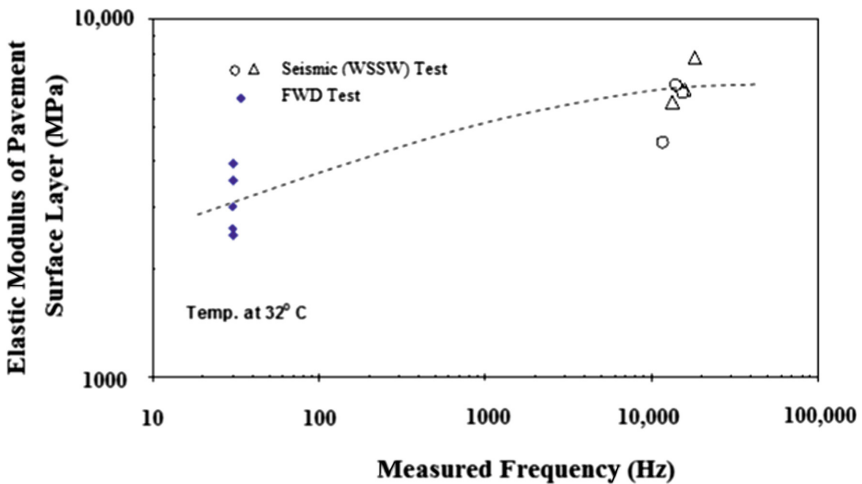


Fig. 12. Influence of frequency on the small strain elastic modulus of asphalt concrete at measured temperature of 32 °C at Purwakarta Road, Indonesia

## 4 Conclusions

The dynamic elastic modulus profile obtained from the proposed technique of the wavelet-spectrogram analysis of surface waves (WSSW) were presented in this paper. This technique improves the conventional SASW measurement testing and was used

for investigation in the complex pavement structure. In this paper, the identification, denoising and reconstruction of the wave response spectrum from seismic surface wave propagation using time-frequency analysis of continuous wavelet transforms is presented. The spectrogram could be used to clearly identify the various events of interest mode of the seismic surface waves. By the simple calculation on phase spectrum from the surface wave data, the elastic modulus of the surface layer can be obtained without the complex calculation of the inversion process. The calculation is easy and can be simply implemented. This technique is also a very sensitive non-destructive testing (NDT) to monitor the change of the modulus of the existing surface and overlay layers.

**Acknowledgments.** This work is part of research project funded by Ministry of Research, Technology and Higher Education, Indonesia and the Universitas Muhammadiyah Yogyakarta (UMY). Their supports are gratefully acknowledged. We would also like to thank Dr. Siegfried (Puslitbang Jalan, Bandung) and research assistants for their assistance during field works.

## References

- Al-Hunaidi, M.O.: Difficulties with phase spectrum unwrapping in spectral analysis of surface waves nondestructive testing of pavements. *Can. Geotech. J.* (1992). doi:[10.1139/t92-055](https://doi.org/10.1139/t92-055)
- Foufoula-Georgiou, E., Kumar, P.: *Wavelets in Geophysics*. Academic Press, Cambridge (1995)
- Ganji, V., et al.: Automated inversion procedure for spectral analysis of surface waves. *J. Geotech. Geoenviron. Eng. ASCE* (1998). doi:[10.1061/\(ASCE\)1090-0241\(1998\)124:8\(757\)](https://doi.org/10.1061/(ASCE)1090-0241(1998)124:8(757))
- Hazra, S., Kumar, J.: SASW testing of asphaltic pavement by dropping steel balls. *Int. J. Geotech. Eng.* (2014). doi:[10.1179/1938636213Z.00000000051](https://doi.org/10.1179/1938636213Z.00000000051). Taylor & Francis
- Kim, D.S., et al.: Evaluation of density in layer compaction using SASW method. *Soil Dyn. Earthq. Eng.* (2001). doi:[10.1016/S0267-7261\(00\)00076-2](https://doi.org/10.1016/S0267-7261(00)00076-2). Elsevier
- Rosyidi, S.A.P., et al.: Signal reconstruction of surface waves on SASW measurement using Gaussian derivative wavelet transform. *Acta Geophys.* (2009). doi:[10.2478/s11600-009-0015-8](https://doi.org/10.2478/s11600-009-0015-8). Springer
- Rosyidi, S.A.P.: Comparison between 2-D and 3-D stiffness matrix model simulation of SASW inversion for pavement structure. *Civil Eng. Dimens. J. Civil Eng. Sci. Appl.* **9**(1), 42–48 (2007)
- Rosyidi, S.A.P.: Simultaneous in-situ stiffness and anomalies measurement on pavement subgrade using tomography surface waves technique. *Proced. Eng.* (2015). doi:[10.1016/j.proeng.2015.11.057](https://doi.org/10.1016/j.proeng.2015.11.057). Elsevier
- Rosyidi, S.A.P., Taha, M.R.: Wavelet spectrogram analysis of surface wave technique for dynamic soil properties measurement on soft marine clay site. *Seism. Waves Res. Anal.* (2012). doi:[10.5772/27530](https://doi.org/10.5772/27530). Intech
- Rosyidi S.A.P., et al.: Development of VS-CBR-DCP empirical model for determining dynamic stiffness of pavement base layer using SASW. In: *Proceedings of International Conference on Advanced Characterisation of Pavement and Soil Engineering Materials*, pp. 895–902 (2007)
- Ryden, N., et al.: Multimodal approach to seismic pavement testing. *J. Geotech. Geoenviron. Eng. ASCE* (2004). doi:[10.1061/\(ASCE\)1090-0241\(2004\)130:6\(636\)](https://doi.org/10.1061/(ASCE)1090-0241(2004)130:6(636))
- Stokoe II, K.H., et al.: Characterization of geotechnical sites by SASW method. In: Wood, R.D. (ed.) *Geotechnical Characterization of Sites*, pp. 15–26. Oxford and IBH Publishing Co., New Delhi (1994)



- Tokimatsu, K., et al.: Effects of multiple modes on Rayleigh wave dispersion characteristics. J. Geotech. Eng. ASCE. (1992). doi:[10.1061/\(ASCE\)0733-9410\(1992\)118:10\(1529\)](https://doi.org/10.1061/(ASCE)0733-9410(1992)118:10(1529))
- Yusoff, N.I.M., et al.: Measurements of the Elastic Modulus of Pavement Subgrade Layers Using the SASW and FWD Test Methods. The Baltic Journal of Road and Bridge Engineering. Technika, Vilnius (2015). doi:[10.3846/bjrbe.2015.22](https://doi.org/10.3846/bjrbe.2015.22)

# CERTIFICATE OF PARTICIPATION



THIS ACKNOWLEDGES THAT

**Prof. Sri Atmaja P. Rosyidi**

HAS ATTENDED ALL ACTIVITIES OF THE GEOMEAST 2017 INCLUDING THE WORKSHOPS  
AND SHORT COURSES, AND PRESENTED THE FOLLOWING PAPER

*"Wavelet-Spectrogram Analysis of Surface Wave Technique for Quick NDT  
Measurement on Surface Layer of Pavement"*

✓ **Dr. Hany Farouk Shehata**  
CEO & Founder of SSIGE



A handwritten signature in black ink, appearing to read 'Hany Farouk Shehata'.



International  
Congress &  
Exhibition

# Wavelet-Spectrogram Analysis of Surface NDT Pavement

*by* Geomeast 2017

---

**Submission date:** 05-Mar-2020 02:27PM (UTC+0700)

**Submission ID:** 1269716426

**File name:** GeoMeast\_Springer2017.pdf (1.46M)

**Word count:** 4686

**Character count:** 24595

# 1 Wavelet-Spectrogram Analysis of Surface Wave Technique for Quick NDT Measurement on Surface Layer of Pavement

Sri Atmaja P. Rosyidi<sup>(✉)</sup>

Department of Civil Engineering, Universitas Muhammadiyah Yogyakarta,  
Yogyakarta, Indonesia  
atmaja\_sri@umy.ac.id

**Abstract.** Reliable assessment of in situ pavements stiffness is an important aspect in effectively managing a pavement system. The aim of this paper is to propose the new procedure, namely the wavelet-spectrogram of surface wave (WSSW) technique for non-destructively measurement of elastic modulus on surface layer of a pavement system. Using two receivers, surface wave propagation on pavement surface was recorded and transformed into in frequency domain by wavelet analysis. For this analysis, a derivative Gaussian wavelet was selected as an appropriate mother wavelet for seismic waveform propagating along pavement surface. Thus, an interactive 2-D plot of time-frequency spectrogram consisting of wave-energy spectrum was simultaneously generated. CWT-filtration method was implemented in order to reduce the effect of noisy signal recorded during measurement. From selected wave spectrogram, the unwrapped phase different spectrum was generated to obtain phase velocity which was performed by least-square linear regression. Finally, the elastic modulus of pavement surface layer was calculated from a modified relationship between phase velocity, Poisson ratio and density of pavement surface layer. The results show that the proposed technique is able to measure in situ elastic stiffness of the surface layer. In addition, the change of the surface layer stiffness is also able to be monitored. The stiffness (elastic modulus) produced by the WSSW technique is classified as a modulus at very low strain level.

## 1 Introduction

The spectral-analysis-of-surface-wave (SASW) is a well-known of non-destructive techniques (NDT) in pavement evaluation and geotechnical investigation. The SASW employs the surface waves dispersion in order to determine the shear wave velocity corresponding to stiffness of each layer at pavement and soil profile. The method performs three steps of an elaborated data process, i.e., (1) collecting seismic data, (2) constructing an experimental dispersion curve and (3) conducting an inversion process of the dispersion curve for generating a stiffness profile. The method has been improved and utilized in many civil engineering applications, e.g., site characterization (Stokoe et al. 1994), soil density (Kim et al. 2001), pavement characterization (Rosyidi et al. 2007, Yusoff et al. 2015), soil damping measurement in soft soil sites (Rosyidi and Taha 2012), and asphaltic pavement measurement (Hazra and Kumar 2014, Rosyidi 2015).

© Springer International Publishing AG 2018

L. Mohammad (ed.), *Advancement in the Design and Performance of Sustainable*

*Asphalt Pavements*, Sustainable Civil Infrastructures, DOI 10.1007/978-3-319-61908-8\_19

1 In inversion process, the advanced mathematical approach is required to produce the stiffness profile from a dispersion curve. Reliable inversion procedure using stress-wave propagation theories, i.e., the transfer matrix method, the dynamic stiffness matrix method and the finite difference method should be employed. All the methods require an initial profile model consists of a set of homogeneous layers extending to infinity in the horizontal direction. In each layer of profile, the information such as a thickness, a shear wave velocity, a Poisson's ratio (or compression wave velocity), and a mass density are assigned. Based on the initial profile, a theoretical dispersion curve is calculated using one of these wave propagation theories. The theoretical dispersion curve is then compared with the experimental dispersion curve. If the two dispersion curves do not match, the initial profile (number of layers, layer thickness, shear wave velocity, or any combination) is adjusted, and another theoretical dispersion curve is calculated. The trial-and-error procedure is repeated until the two curves match, and then the associated assumed profile is considered the real profile. In addition, when the SASW method is performed on irregular stiffness profile, i.e., pavement structure, the trial-and-error procedure becomes a difficult analysis and takes longer time in data processing. Moreover, several researchers have reported on difficulties related to surface wave measurements at pavement sites. Most of these difficulties are reported to originate from the influence of higher modes of propagation (Al-Hunaidi 1992, Tokimatsu et al. 1992, Ganji et al. 1998; Ryden et al. 2004).

The seismic surface wave method is not able to separate different modes of propagation on a pavement system and thus measures a superposition of all propagating waves at the specific receiver locations. This superposed effect, often termed apparent phase velocity or pseudophase velocity, changes with distance and has forced the evaluation of the data to take into account the position of the receivers and the superposition of different modes for the inversion of experimental dispersion curves. Ryden et al. (2004) proposed a new approach in seismic pavement testing where the different modes of propagation are separated, thereby potentially clarifying some of the noted difficulties with the SASW method applied to pavement testing. Their approach is based on the multichannel analysis of surface wave (MASW) data processing technique. However, due to complexity in surface wave analysis, application of these methods on pavement evaluation is still relatively limited. On the other hand, in pavement evaluation system, the need of accurate, cost-effective and non-destructive evaluation is becoming ever important because the rehabilitation and management of roads is becoming increasingly difficult due to the increasing number of aging roads and limited budgets. As well, for practical purpose, pavement engineer usually needs a quick and relatively effortless analysis for determining the structural condition of pavement surface layers.

In this paper, a new procedure in a surface wave technique which is using continuous wavelet transform combined with the elastic stiffness formulation for obtaining the phase velocity is introduced. This method is namely the wavelet-spectrogram of surface wave (WSSW) technique. The time-frequency decomposition of continuous wavelet transform (CWT) on seismic signals is employed to characterize the phase information of phase different spectrum. It provides a reliable information of wave spectrum in the pavement profile. An algorithm on phase different calculation in this analysis aims to avoid the use of a complex inversion algorithm to obtain the elastic

modulus of the pavement surface layer. In the SASW method, data analysis and processing in frequency domain has been carried out by fast Fourier transforms (FFT). However, due to Fourier transform works by expressing any arbitrary periodic function of time with period as sum a set of sinusoidal, this analysis becomes inconsistent and is unable to preserve the time dependence and describe the evolutionary spectral characteristics of non-stationary processes (Rosyidi et al. 2009). Wavelet analysis is becoming an effective tool for analyzing localized variations of power within a time series. By decomposing a time series into time-frequency spectrum (TFW), one is able to determine both the dominant modes of variability and how those modes vary in time. A typical result from a case study is presented herein for the structural assessment of an existing asphalt concrete (AC) pavement in Purwakarta, West Java, Indonesia.

### 1.1 Continuous Wavelet Transform

The continuous wavelet transform (CWT) has been used in many studies in geophysics (Foufoula-Georgiou and Kumar 1995) and civil engineering application (Rosyidi et al. 2009). The continuous wavelet transform (CWT) technique is an alternative tool for localizing the interested frequency of seismic signal processing particularly in non-stationary problems. Wavelets dilate in such a way that the time support changes for different frequency. When the time support increases or decreases, the frequency support of the wavelet is shifted toward high or low frequencies, respectively. Therefore, as the frequency resolution increases, the time resolution decreases and vice versa. The characteristic of time-frequency resolution creates the CWT technique useful for non-stationary seismic analysis.

A wavelet is defined as a function of  $\psi(t) \in L^2(\mathfrak{R})$  with a zero mean, which is localized in both time and frequency. By dilating and translating the wavelet  $\psi(t)$ , it can be used to produce a family of wavelets as:

$$\psi_{\sigma,\tau}(t) = \frac{1}{\sqrt{\sigma}} \psi\left(\frac{t-\tau}{\sigma}\right) \quad (1)$$

where  $\sigma$  is the dilation parameter or scale and  $\tau$  is the translation parameter ( $\sigma, \tau \in \mathfrak{R}$  and  $\sigma \neq 0$ ). The wavelet has also various wavelet shape used for signal analysis which is called the mother of wavelet, i.e., Gaussian, Morlet, Paul and Mexican Hat. An appropriate selection of wavelet shape signal analysis depends on the seismic waveforms.

The CWT is defined as the inner product of the family wavelets  $\Psi_{\sigma,\tau}(t)$  with the signal of  $f(t)$  which is given as:

$$F_W(\sigma, \tau) = \langle f(t), \psi_{\sigma,\tau}(t) \rangle = \int_{-\infty}^{\infty} f(t) \frac{1}{\sqrt{\sigma}} \bar{\psi}\left(\frac{t-\tau}{\sigma}\right) dt \quad (2)$$

where  $\bar{\psi}$  is the complex conjugate of  $\psi$ ,  $F_W(\sigma, \tau)$  is the time-scale map.

**1** In this study, the mother wavelet of the Gaussian Derivative (GoD) was used. The real component of the GoD wavelet in the time and frequency domains is defined as follows:

$$\psi_0(t) = \frac{(-1)^{m+1}}{\sqrt{\Gamma(m + \frac{1}{2})}} \frac{d^m}{dt^m} \left( e^{-t^2/2} \right) \quad (3)$$

$$\hat{\psi}_0(s\omega) = -\frac{t^m}{\sqrt{\Gamma(m + \frac{1}{2})}} (s\omega)^m \left( e^{-(s\omega)^2/2} \right) \quad (4)$$


where  $m$  is the wave number and  $\Gamma$  is the Gamma function. The complex wavelet is generated by the addition of a Heaviside function in the frequency domain. This wavelet decays with the square root of the gamma function. The GoD has wavelet's derivative order that can be varied in order to get the best resolution of the waveform.

## 2 Research Method

### 2.1 Field Measurement

In field measurement of the WSSW method, a set of ball bearing with weight from 5 to 15 g was used as an impact source to generate seismic waves on the surface layer of pavement. Generated seismic waves were then detected using two high frequency accelerometers. Consequently, the signals were recorded using an ADT analog-digital acquisition connected to a notebook computer for post processing (Fig. 1). In this study, two configurations of mid-point receiver spacing and the receiver-source spacings were employed in order to sample different depths of pavement surface. The configuration of mid-point receiver spacings was described in Fig. 2. The receiver spacing ( $d_2$ ) was obtained as a distance which the length is less than and/or equal to the thickness ( $H$ ) of pavement surface layer. Whereas, the distance between a source and first receiver ( $d_1$ ) was set as equal to receivers spacing ( $d_2$ ). Due to the interested pavement area in measurement was asphaltic surface layer, the short receiver spacings of 5, 10 and 15 cm with a high frequency source were only used. In the test, repetition procedure (forward and backward) until at least 4 to 6 times in each receiver spacing measurement should be employed in order to minimize the effect of internal phase shift between receivers and to enhance a good average of received signals.

Beside the WSSW test, the SASW measurement was also carried out at same sites of existing road pavement in Purwakarta, West Java, Indonesia. The pit test was also conducted to acquire the information of a pavement profile. From the pit test, the pavement structure consists of an asphalt concrete (AC) layer (18 cm), crushed stone of base course (10 cm), sub-base course (30 cm) over a subgrade layer.

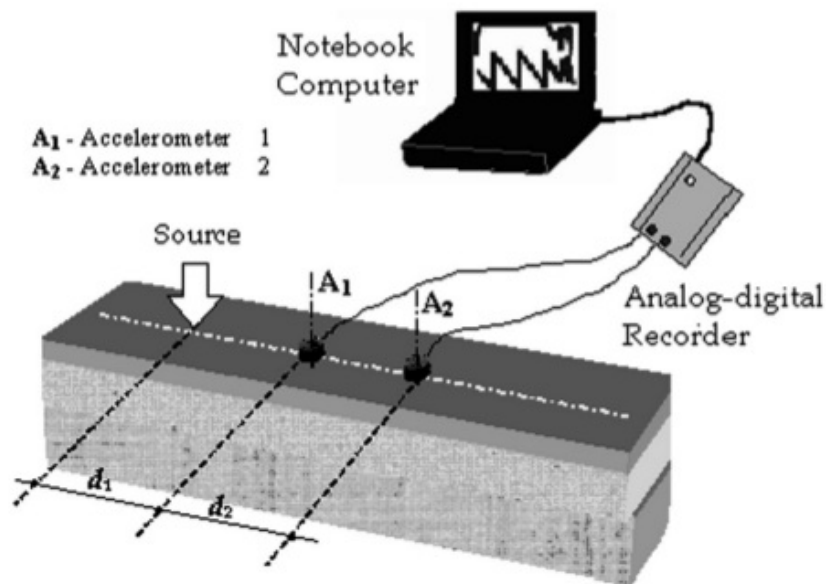

**1** Fig. 1. Experimental set up of WSSW measurement on a pavement structure

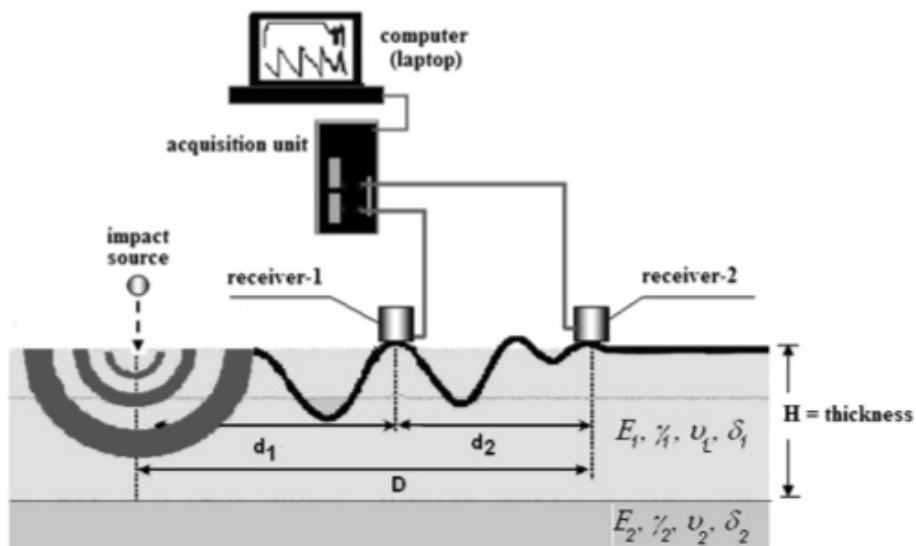


Fig. 2. Mid-point receivers configuration of WSSW measurement on pavement structure

## 2.2 Data Analysis and Process

A proposed procedure of the WSSW method consists of seismic data analysis using continuous wavelet transform and elastic modulus calculation of elastic linear model on pavement surface layer which is described as follows:

1. The seismic wave data are collected from field measurement using a configuration of the mid-point receiver spacings.
2. The time-frequency spectrum analysis based on continuous wavelet transform of Gaussian Derivative (DoG) mother wavelet is carried out for two signal waveforms recorded from field measurement. By decomposing a time series of seismic



waveform into time-frequency (TF) spectrogram, the dominant modes of variability and how those modes vary in time can be determined very well.

3. Phase information of the transfer function (phase spectrum) are then determined from both TF spectrograms. The data informs the time difference of wave propagating from first to second receiver. A mathematical expression for calculating phase spectrum from TF spectrogram is defined by (Rosyidi and Taha 2012):

$$H(f) = \frac{Y(f)}{X(f)} \approx \frac{W_{f(u,s)}^Y}{W_{f(u,s)}^X} = \frac{\int_{-\infty}^{\infty} Y(t) \frac{1}{\sqrt{\sigma}} \psi * \left(\frac{t-\tau}{\sigma}\right) dt}{\int_{-\infty}^{\infty} X(t) \frac{1}{\sqrt{\sigma}} \psi * \left(\frac{t-\tau}{\sigma}\right) dt} \tag{5}$$

where,

$X(f)$  = spectrum input of signal,  $X(t)$ , from first receiver,  
 $Y(f)$  = spectrum output of signal,  $Y(t)$ , from second receiver,

$$W_{f(u,s)}^Y = \int_{-\infty}^{\infty} Y(t) \frac{1}{\sqrt{s}} g\left(\frac{t-u}{s}\right) e^{-i\xi(t-u)} dt \tag{6}$$

$$W_{f(u,s)}^X = \int_{-\infty}^{\infty} X(t) \frac{1}{\sqrt{s}} g\left(\frac{t-u}{s}\right) e^{-i\xi(t-u)} dt \tag{7}$$

From Eq. 7, the phase spectrogram in time-frequency domain can be obtained by:

$$H(u, s) = \frac{W_f^{XY}(u, s)}{W_f^{XX}(u, s)} = \frac{|W_f^{XY}(u, s)| e^{i(\theta_Y(a,b) - \theta_X(a,b))}}{W_f^X(u, s)^* \times W_f^X(u, s)} \tag{8}$$

Thus, phase different is obtained from the ratio of the imaginary to real part of the phase spectrogram which is expressed as:

$$\phi = \tan^{-1} \left( \frac{\Im H(u, s)}{\Re H(u, s)} \right) \tag{9}$$

4. The coherence function is used to visually inspect the quality of signals being recorded in the field and have a real value between zero and one in the range of frequencies being measured. The value of one indicates a high signal-to-noise ratio (i.e., perfect correlation between the two signals) while values of zero represents no correlation between the two signals. The coherence function is a ratio of the output power caused by the measured input to the total measured output which is defined as:

$$\gamma^2(f) = \frac{G_{yx}(f) \cdot G_{yx}^*(f)}{G_{xx}(f) \cdot G_{yy}(f)} \quad (10)$$

5. A linear relationship between the phase different and frequency from the transfer function spectrum is then derived. The phase velocity is examined as a function of distance from the slope value ( $m$ ). This relationship can be written as:

$$\phi = \left| \frac{360D}{V_{ph}} \right| f = mf \quad (11)$$

By Eq. 11, one can easily determine  $V_{ph}$  by performing a least-square linear regression over the frequency range in the transfer function spectrum and the slope of the best-fit line ( $m$ ) can be obtained. The phase velocity of surface wave propagation is independent of the wavelength for up to a wavelength approximately equal to thickness of the uppermost layer. The range of wavelength to be used can be estimated from the phase velocities ( $V_{ph}$ ) of the material anticipated at the site:

$$\lambda = \frac{V_{ph}}{f} \quad (12)$$

where  $f$  is the frequency.

6. If one simply generates high frequency waves and assumes that properties of the uppermost layer are uniform, the dynamic elastic moduli of the pavement materials can easily be determined as follows:

$$E = 2 \frac{\gamma}{g} V_s^2 (1 + \mu) = \frac{\gamma}{g} |KV_{ph}|^2 \quad (13)$$

$$K = (1.13 - 0.16\mu) \sqrt{\frac{2(1 - \mu)}{(1 - 2\mu)}} \quad (14)$$

where  $E$  is the dynamic elastic modulus, respectively,  $V_s$  is the shear wave velocity,  $V_{ph}$  is the phase wave velocity,  $g$  is the gravitational acceleration,  $\gamma$  is the total unit weight of the material and  $\mu$  is the Poisson's ratio.

### 3 Results and Discussion

#### 3.1 Stiffness and Elastic Modulus

The WSSW measurements were carried out at 12 sites on existing asphalt pavements. A typical result of received signals from field measurement was shown in Fig. 3. The body waves (Primary and Secondary wave) and surface wave (Rayleigh wave) are clearly shown in both signal recordings. Therefore, the Gaussian Derivative (GoD) continuous wavelet transform (CWT) was employed on signals for generating a

1 time-frequency (TF) plot. Both CWT plots may overcome on identification problem of the spectral characteristics of non-stationary signals measured in two receivers. The typical CWT spectrogram for received signals with an improved time-frequency resolution is shown in Fig. 4. From Fig. 4, two main energy events at different frequency bands were also clearly detected which may result in both low and higher mode of seismic waves. It is able to observed that lower frequency energy was found in the range of 2.8–16 kHz in CWT spectrogram. This spectrum range is identified as surface wave signals. The level and frequency range of these signals were determined by independent-measurement of high level energy in surface wave propagation (up to 60% of total wave energy). Thus, the other energy event is identified as wave mode from direct and reflected body waves which was found in more than 20 kHz. The dominant wave energy found in CWT spectrogram at interested frequency range of surface waves can be clearly captured. The TF of GoD-CWT provides good resolutions at high frequencies of signals. It is also effective in the detection of frequency bandwidth of wave groups using various derivation order of this mother wavelet (GoD).



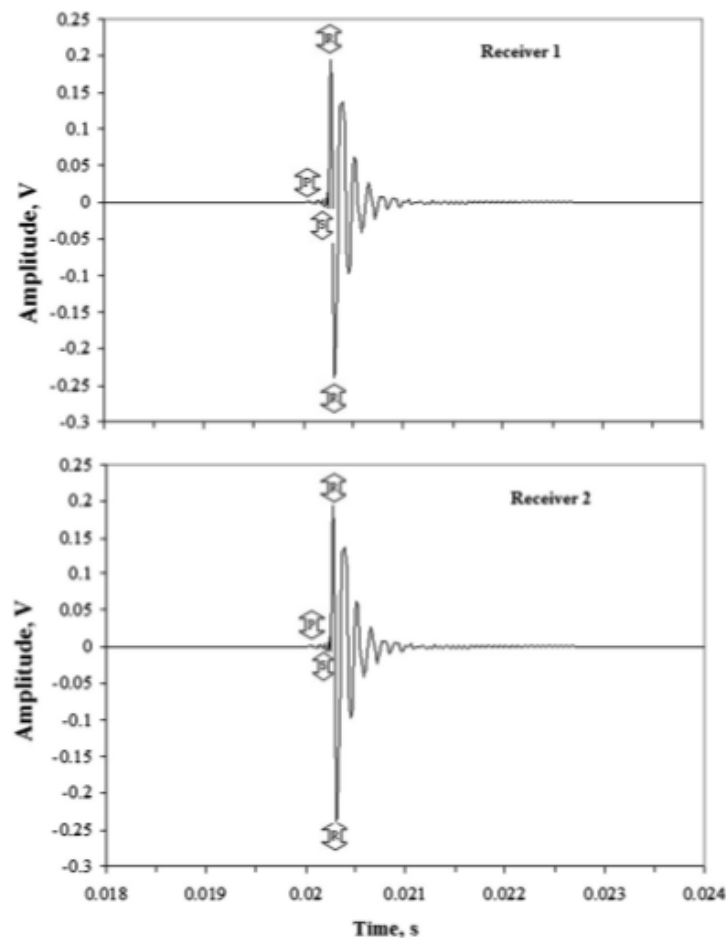


Fig. 3. Signal from WSSW measurement on a pavement structure

Based on both TF spectrograms (Fig. 4), the phase different between two signals for every wave frequency were then calculated. As a result, a transfer function spectrum on wrapped phase different curve was obtained as given in Fig. 5. The phase data

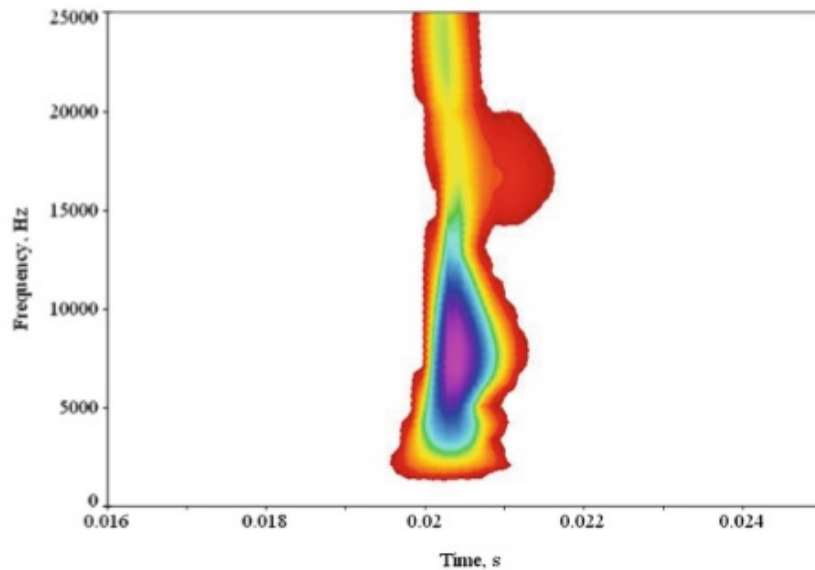

(a) CWT Spectrogram from receiver 1

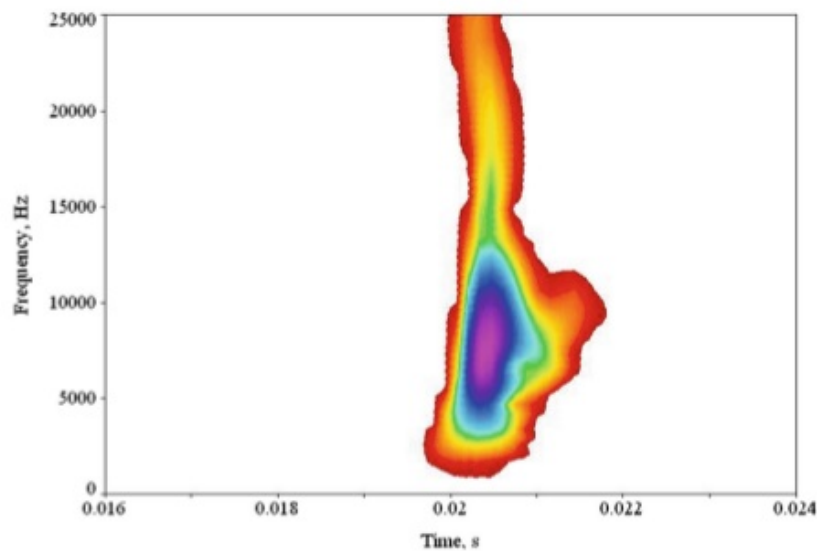


(b) CWT Spectrogram from receiver 2


**Fig. 4.** Time-frequency plot of received signals from measurement

oscillates between  $-\pi$  and  $\pi$  radian ( $-180$  and  $180$  degrees). This is the standard illustration of spectrum presenting phase data because the detail variation in data can be observed in a small space.

Figure 5 also shows that the phase different curve reveals a smooth trend of variation in phase with frequency up to a frequency of 25 kHz. It indicates the high-frequency surface waves were detected representing the high stiffness of the asphalt concrete surface layer on a pavement structure. The quality of phase data is also controlled by the coherence function. As shown in Fig. 6, the phase data up to frequency of 20 kHz have the value of coherence magnitude above 0.98.

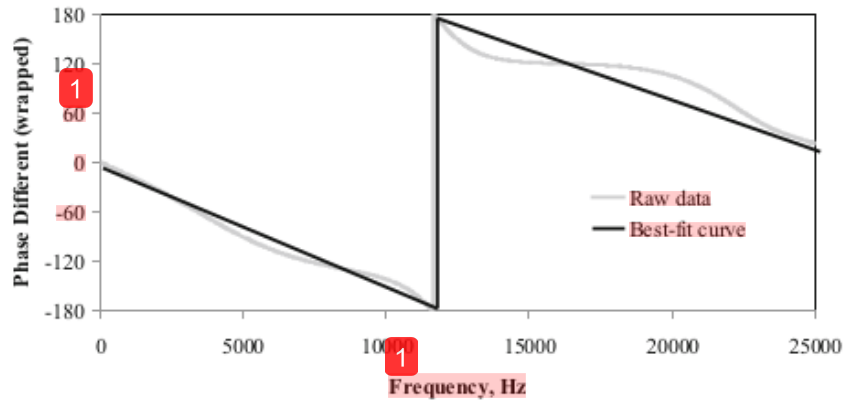


**Fig. 5.** Comparison between raw data and best-fit curve of wrapped transfer function spectrum from measurement

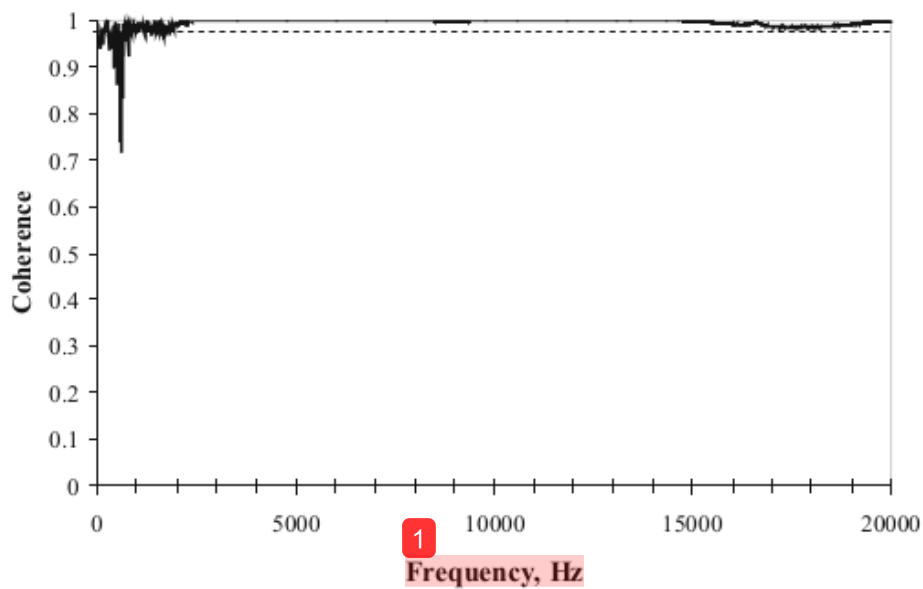

**Fig. 6.** Coherent function spectrum of received signals from measurement

In order to obtain the modulus value of the surface layer, the smoothed fitting process of weighing function was used. The fitted curve between the raw and the smoothed phase spectrum is shown in Fig. 5. Thus, the phase data is unwrapped by adding the number cycles to each phase. The unwrapped of the raw phase spectrum is also shown in Fig. 7. The unwrapped phase spectrum is smoothed by the linear regression as the best fit curve to the raw data. The slope of the line is more or less constant with frequency. A line is fitted to the curve in the range of the frequency corresponding to wavelengths shorter than the thickness of the surface layer. Slope value of the line can be used to determine the elastic modulus of the surface layer of the pavement profile using Eqs. 11, 13 and 14.

From Fig. 7, the slope ( $m$ ) of best-fit curve is found to be 0.0140. Consequently, the phase velocity can be calculated using Eq. 13 which is found to be 1028.57 m/s. Based on the phase velocity, field configuration data and material parameters, such as of

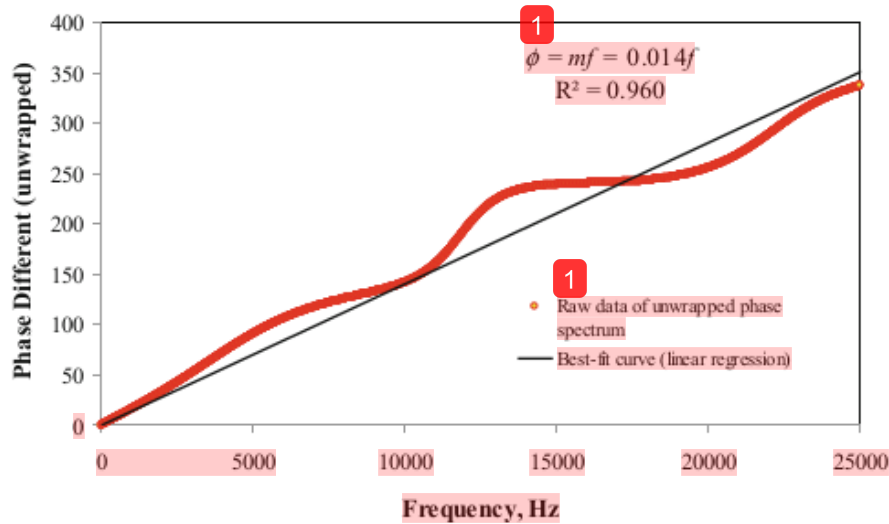


**Fig. 7.** Comparison between raw data and best-fit curve of unwrapped transfer function spectrum from measurement and slope analysis to obtain  $m$  value

receiver spacing ( $d_2$ ) of 5 cm, Poisson's ratio of asphaltic layer of 0.25 and unit weight for pavement material (AC) of  $2,200 \text{ kg/m}^3$ , the elastic modulus of asphaltic (AC) surface layer is obtained as  $845,662,040.80 \text{ kg/m}^2$  or  $8456.62 \text{ MPa}$ .


The result shows that the elastic modulus of AC layer can be easily determined using the WSSW technique. However, the value of elastic modulus presented is relatively high. It is due to the seismic technique measures the dynamic stiffness at very low strain level (less than 103%). In this level, the material modulus behavior can be assumed as a constant and have only a maximum value. To illustrate the usefulness and sensitivity of this approach in testing the surface layer, changes in the stiffness of the existing surface and the overlay layer of the pavement were measured in situ. Figure 8 shows that the different stiffness of an existing and overlay surface layer from the measured profile can be investigated well. Based on these results, it can be summarized that the stiffness changes in the surface layer were easily, non-destructively, and fast measured by the WSSW technique.

### 3.2 Validation with the SASW Method

In order to validate the results from the WSSW test, the spectral-analysis-of-surface-wave (SASW) analysis was conducted at same locations of a road pavement. In this method, a set of transient impact sources was used to generate surface wave energy that propagates horizontally near the surface layer of the pavement. The phase differences of signal data were obtained from the cross-power spectrum. Thus, the phase information was then unwrapped to produce the dispersion curve of the phase velocity versus wavelength. An inversion process was then iteratively employed to confirm the experimental dispersion curve from the theoretical model established. A 3-D stiffness matrix model (Rosyidi 2007) was employed in the SASW inversion analysis. Final stiffness profile was obtained after 16 times of iteration with the root-mean-square error (RMS) of  $35.47 \text{ m/s}$  or average deviation of about  $5.92\%$ .

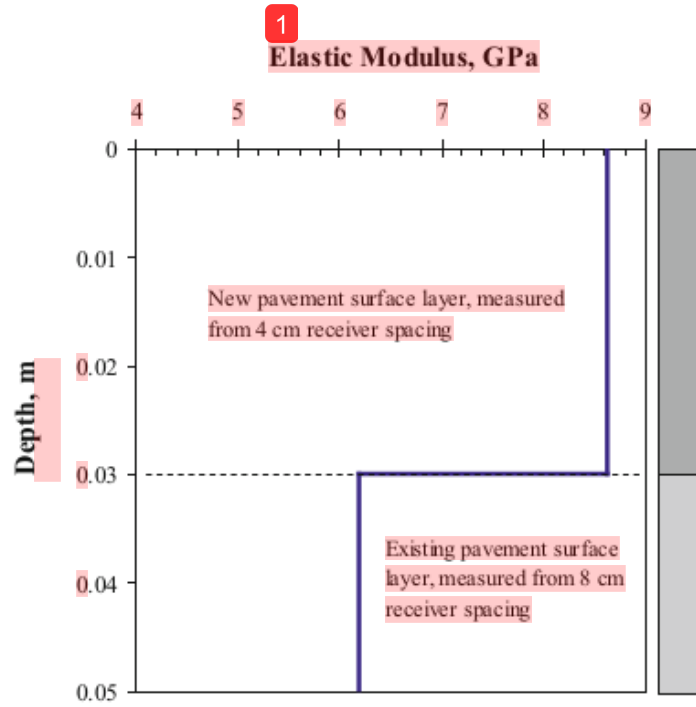


**Fig. 8.** Comparison between elastic modulus of an overlay and existing surface layer at pavement roads, Indonesia

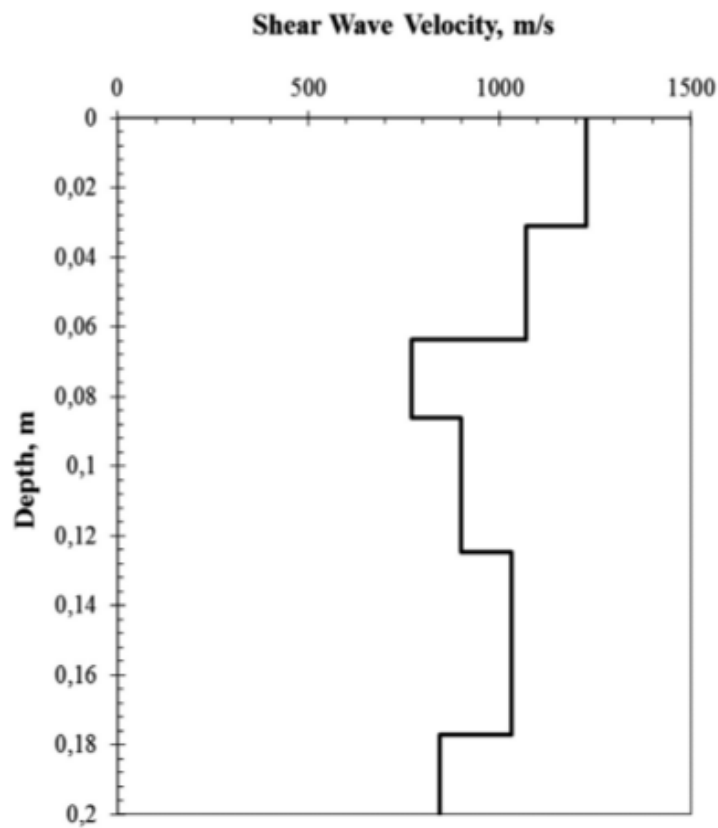

**Fig. 9.** The shear wave velocity profile from inversion of the experimental dispersion curve


The equivalent shear wave profile from the result of the inversion is shown in Fig. 9 and using the dynamic material equation, its equivalent dynamic elastic modulus profile is given in Fig. 10. A modulus profile as shown in Fig. 10 is only given to 10 cm depth of pavement structure due to the asphaltic layer was indicated at this level. A good agreement of elastic modulus resulted from the WSSW and the SASW method is also presented in Fig. 10. The result shows that the difference between both methods is calculated at 0.01% and 1.14% for first and second layer of pavement surface layer, respectively.

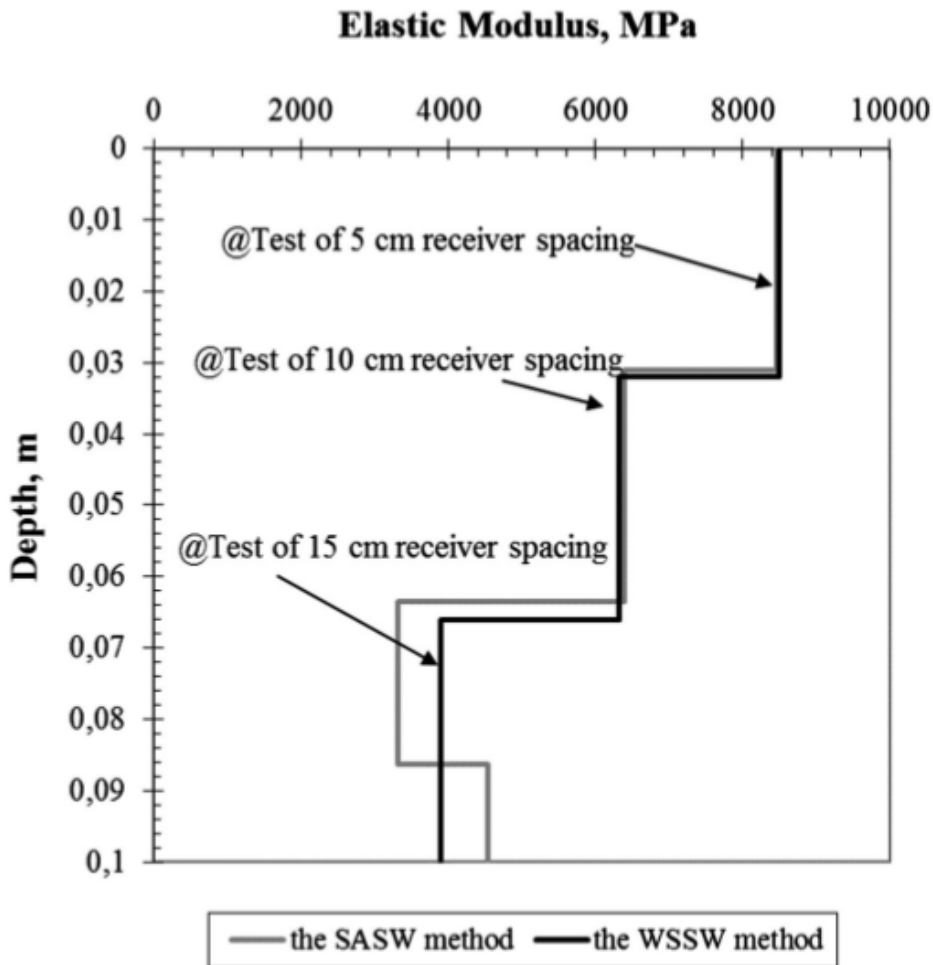

**Fig. 10.** The dynamic elastic modulus of the pavement profile from the SASW method and its comparison with the WSSW method

The falling weight deflectometer (FWD) method was also employed to validate the elastic modulus of pavement surface layer from the WSSW test. The elastic modulus of pavement surface layer obtained from both measurements is shown in Fig. 11. The elastic modulus obtained from the WSSW is higher comparison with value determined by the FWD. As mentioned earlier, the modulus measured at very low strain levels associated with surface wave method is in maximum value and it is independent from strain amplitude. In addition, the high frequency used in the seismic result in higher values of stiffness for pavement material. In the case of FWD, the modulus was measured at frequency of around 30 Hz (Fig. 12).



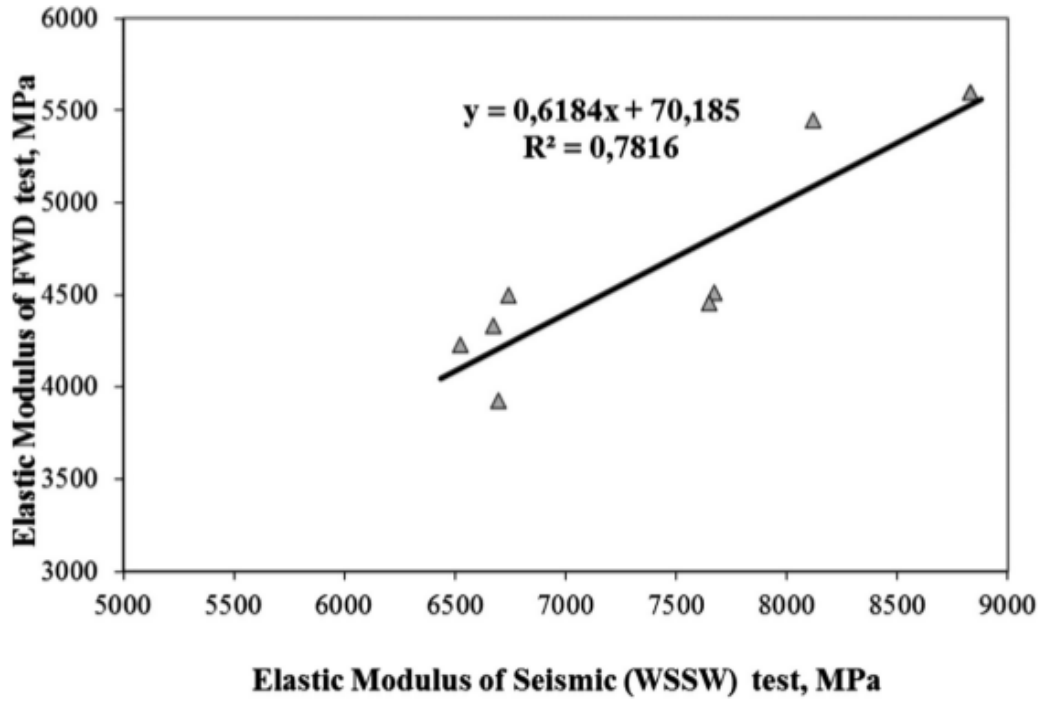

**1** Fig. 11. Comparison elastic modulus of surface layers from the SASW test compared to the FWD test at Purwakarta State Road, Indonesia

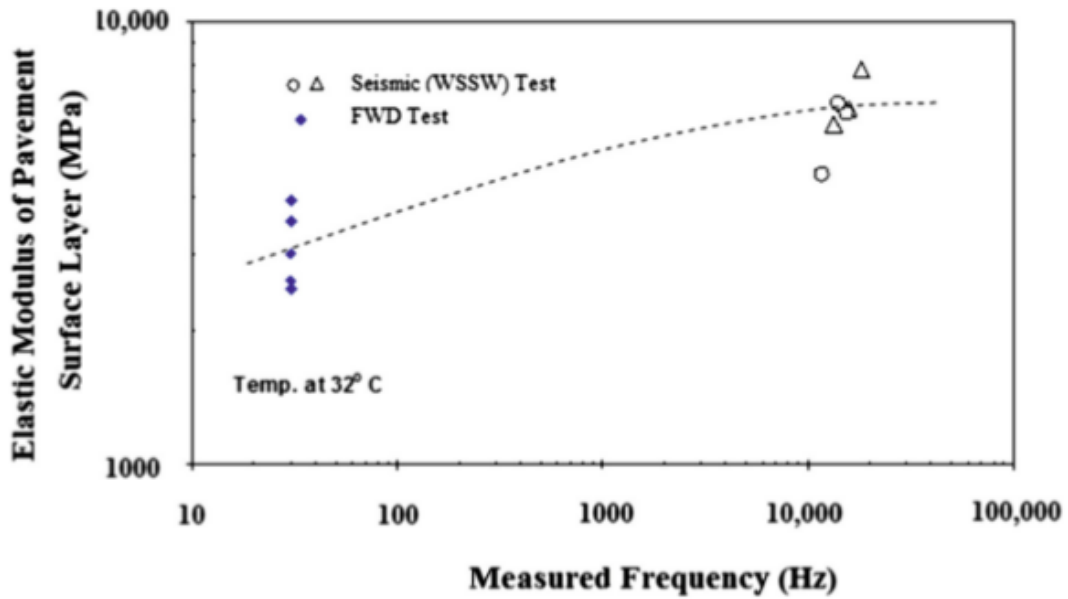


Fig. 12. Influence of frequency on the small strain elastic modulus of asphalt concrete at measured temperature of 32 °C at Purwakarta Road, Indonesia

#### 4 Conclusions

The dynamic elastic modulus profile obtained from the proposed technique of the wavelet-spectrogram analysis of surface waves (WSSW) were presented in this paper. This technique improves the conventional SASW measurement testing and was used

1 for investigation in the complex pavement structure. In this paper, the identification, denoising and reconstruction of the wave response spectrum from seismic surface wave propagation using time-frequency analysis of continuous wavelet transforms is presented. The spectrogram could be used to clearly identify the various events of interest mode of the seismic surface waves. By the simple calculation on phase spectrum from the surface wave data, the elastic modulus of the surface layer can be obtained without the complex calculation of the inversion process. The calculation is easy and can be simply implemented. This technique is also a very sensitive non-destructive testing (NDT) to monitor the change of the modulus of the existing surface and overlay layers.

**Acknowledgments.** This work is part of research project funded by Ministry of Research, Technology and Higher Education, Indonesia and the Universitas Muhammadiyah Yogyakarta (UMY). Their supports are gratefully acknowledged. We would also like to thank Dr. Siegfried (Puslitbang Jatan, Bandung) and research assistants for their assistance during field works.

## References

- Al-Hunaidi, M.O.: Difficulties with phase spectrum unwrapping in spectral analysis of surface waves nondestructive testing of pavements. *Can. Geotech. J.* (1992). doi:[10.1139/t92-055](https://doi.org/10.1139/t92-055)
- Foufoula-Georgiou, E., Kumar, P.: *Wavelets in Geophysics*. Academic Press, Cambridge (1995)
- Ganji, V., et al.: Automated inversion procedure for spectral analysis of surface waves. *J. Geotech. Geoenviron. Eng. ASCE* (1998). doi:[10.1061/\(ASCE\)1090-0241\(1998\)124:8\(757\)](https://doi.org/10.1061/(ASCE)1090-0241(1998)124:8(757))
- Hazra, S., Kumar, J.: SASW testing of asphaltic pavement by dropping steel balls. *Int. J. Geotech. Eng.* (2014). doi:[10.1179/1938636213Z.00000000051](https://doi.org/10.1179/1938636213Z.00000000051). Taylor & Francis
- Kim, D.S., et al.: Evaluation of density in layer compaction using SASW method. *Soil Dyn. Earthq. Eng.* (2001). doi:[10.1016/S0267-7261\(00\)00076-2](https://doi.org/10.1016/S0267-7261(00)00076-2). Elsevier
- Rosyidi, S.A.P., et al.: Signal reconstruction of surface waves on SASW measurement using Gaussian derivative wavelet transform. *Acta Geophys.* (2009). doi:[10.2478/s11600-009-0015-8](https://doi.org/10.2478/s11600-009-0015-8). Springer
- Rosyidi, S.A.P.: Comparison between 2-D and 3-D stiffness matrix model simulation of SASW inversion for pavement structure. *Civil Eng. Dimens. J. Civil Eng. Sci. Appl.* **9**(1), 42–48 (2007)
- Rosyidi, S.A.P.: Simultaneous in-situ stiffness and anomalies measurement on pavement subgrade using tomography surface waves technique. *Proced. Eng.* (2015). doi:[10.1016/j.proeng.2015.11.057](https://doi.org/10.1016/j.proeng.2015.11.057). Elsevier
- Rosyidi, S.A.P., Taha, M.R.: Wavelet spectrogram analysis of surface wave technique for dynamic soil properties measurement on soft marine clay site. *Seism. Waves Res. Anal.* (2012). doi:[10.5772/27530](https://doi.org/10.5772/27530). Intech
- Rosyidi S.A.P., et al.: Development of VS-CBR-DCP empirical model for determining dynamic stiffness of pavement base layer using SASW. In: *Proceedings of International Conference on Advanced Characterisation of Pavement and Soil Engineering Materials*, pp. 895–902 (2007)
- Ryden, N., et al.: Multimodal approach to seismic pavement testing. *J. Geotech. Geoenviron. Eng. ASCE* (2004). doi:[10.1061/\(ASCE\)1090-0241\(2004\)130:6\(636\)](https://doi.org/10.1061/(ASCE)1090-0241(2004)130:6(636))
- Stokoe II, K.H., et al.: Characterization of geotechnical sites by SASW method. In: Wood, R.D. (ed.) *Geotechnical Characterization of Sites*, pp. 15–26. Oxford and IBH Publishing Co., New Delhi (1994)

1

Tokimatsu, K., et al.: Effects of multiple modes on Rayleigh wave dispersion characteristics. J. Geotech. Eng. ASCE. (1992). doi:[10.1061/\(ASCE\)0733-9410\(1992\)118:10\(1529\)](https://doi.org/10.1061/(ASCE)0733-9410(1992)118:10(1529))

Yusoff, N.I.M., et al.: Measurements of the Elastic Modulus of Pavement Subgrade Layers Using the SASW and FWD Test Methods. The Baltic Journal of Road and Bridge Engineering. Technika, Vilnius (2015). doi:[10.3846/bjrbe.2015.22](https://doi.org/10.3846/bjrbe.2015.22)

# Wavelet-Spectrogram Analysis of Surface NDT Pavement

## ORIGINALITY REPORT

95%

SIMILARITY INDEX

%

INTERNET SOURCES

95%

PUBLICATIONS

%

STUDENT PAPERS

## PRIMARY SOURCES

1

Sri Atmaja P. Rosyidi. "Chapter 19 Wavelet-Spectrogram Analysis of Surface Wave Technique for Quick NDT Measurement on Surface Layer of Pavement", Springer Science and Business Media LLC, 2018

Publication

93%

2

M. O. Al-Hunaidi. "Difficulties with phase spectrum unwrapping in spectral analysis of surface waves nondestructive testing of pavements", Canadian Geotechnical Journal, 1992

Publication

2%

Exclude quotes Off

Exclude matches Off

Exclude bibliography Off